



## Fabrication of nano and micro structured polymer foils by roll-to-roll-extrusion coating

**Murthy, Swathi; Matschuck, M. ; Pranov, H.; Kofod, G.; Pedersen, Henrik; Taboryski, Rafael**

*Published in:*  
Book of Abstracts. DTU's Sustain Conference 2015

*Publication date:*  
2015

*Document Version*  
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

*Citation (APA):*  
Murthy, S., Matschuck, M., Pranov, H., Kofod, G., Pedersen, H., & Taboryski, R. (2015). Fabrication of nano and micro structured polymer foils by roll-to-roll-extrusion coating. In *Book of Abstracts. DTU's Sustain Conference 2015* Article P-5 Technical University of Denmark.

---

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

## Fabrication of nano and micro structured polymer foils by roll-to-roll-extrusion coating.

S.Murthy<sup>1,3</sup>, M.Matschuck<sup>1</sup>, H. Pranov<sup>1</sup>, G. Kofod<sup>1</sup>, H. Pedersen<sup>3</sup>, R.Taboryski<sup>2</sup>

1. InMold A/S, Gregersensvej 6H, DK - 2630 Taastrup, Denmark

2. Department of Micro- and Nanotechnology, Technical University of Denmark

3. Department of Photonics Engineering, Technical University of Denmark

E-mail: [smurthy@fotonik.dtu.dk](mailto:smurthy@fotonik.dtu.dk)

We suggest a novel roll-to-roll process for nano- and microstructuring, which will accelerate the integration of nanostructured materials in a broad range of applications, including optical, technical and functional surfaces and devices. Possible applications may even include cast molding of advanced materials for photovoltaic, thermo-electric, electro-active and electro-storage applications, where nanostructuring often leads to improved properties. The process is known as roll-to-roll extrusion coating (R2R-EC : in the packaging industry commonly referred to as co-extrusion), and is widely used for production of smooth polymer films, but has not previously been employed for replication of nanostructures (shown in figure 1). Among benefits of the process are availability of a wide range of commercial extruders, off-the-shelf extrusion grade polymers, functional additives, polymeric materials with good diffusion barrier properties, and the overall maturity of the technology. In roll-to-roll extrusion coating a molten polymer film is extruded through a flat nozzle forming a melt curtain, then stretched in air, and finally laminated onto a carrier foil. The lamination process takes place as the melt curtain is squeezed between a cooling roller and a rubber counter roller. By attaching a nanostructured metal sheet to the surface of the cooling roller, the relief structure from the sheet can be replicated onto a plastic foil. We have demonstrated that nanostructures with typical linewidths in the range 100 - 400 nm are best replicated using semi-crystalline polymers such as polypropylene (PP), running at high roller line-speed of 60 meters per minute, and high cooling roller temperature of 70° C. Replication in other common polymers like polyethylene (PE) and polystyrene (PS) was not possible for nanostructures. However, structures with linewidths and depths above ca. 400 nm were more forgiving and allowed for a wider range of materials. For such microstructures, it was found that process parameters had to be individually optimized for each pattern, indicating that viscoelastic flow into the relief plays a more important role.

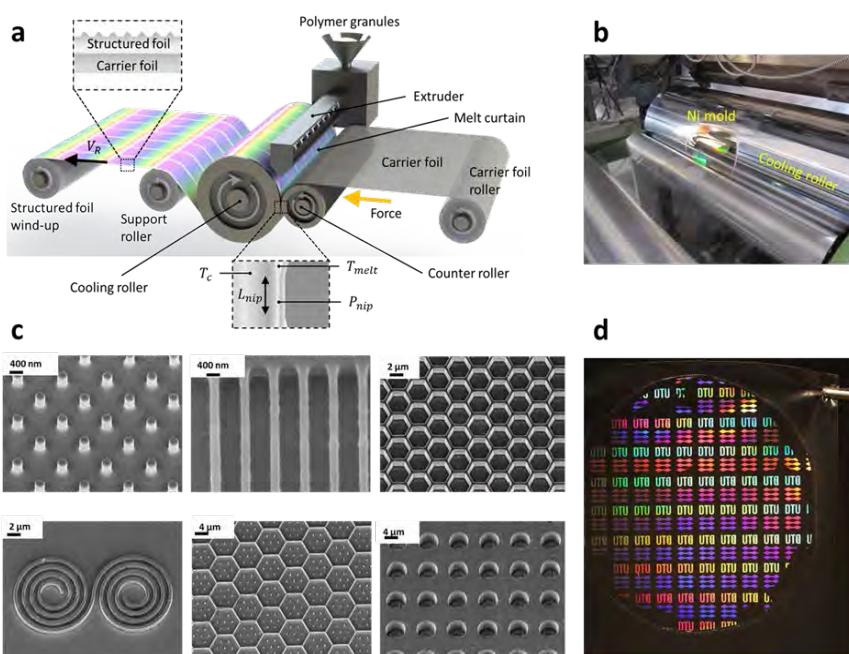


Figure 1. a: Schematic of R2R-EC process. b: Photograph of the cooling roller with the Ni mold mounted. c: Scanning electron micrographs of structures with various shapes, linewidths ranging from 400 nm to  $\geq 1 \mu\text{m}$ , and aspect ratios  $\geq 1$  replicated in PP by R2R-EC. Images were taken at a 30° tilt angle. d: Example of an application of the technology; diffraction grading pattern with DTU logo produced by R2R-EC. The pattern was originated from a 100 mm Si wafer, electroformed into a Ni mold, and replicated by R2R-EC on PP foil.