



In situ environmental transmission electron microscope investigation of NiGa nanoparticle synthesis

Damsgaard, Christian Danvad; Duchstein, Linus Daniel Leonhard; Elkjær, Christian Fink; Sharafutdinov, Irek; Dahl, Søren; Wagner, Jakob Birkedal

Published in:
MC 2011 Kiel

Publication date:
2011

[Link back to DTU Orbit](#)

Citation (APA):

Damsgaard, C. D., Duchstein, L. D. L., Elkjær, C. F., Sharafutdinov, I., Dahl, S., & Wagner, J. B. (2011). In situ environmental transmission electron microscope investigation of NiGa nanoparticle synthesis. In *MC 2011 Kiel: Microscopy Conference 2011* (pp. IM6-CDD). DGE – German Society for Electron Microscopy. <http://www.mc2011.de/>

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

***In situ* environmental transmission electron microscope investigation of NiGa nanoparticle synthesis**

C.D. Damsgaard¹, L.D.L. Duchstein¹, C.F. Elkjær², I. Sharafutdinov², S. Dahl², and J.B. Wagner¹

1. Center for Electron Nanoscopy, Technical University of Denmark, DK-2800 Lyngby, Denmark

2. Department of Physics, Technical University of Denmark, DK-2800 Lyngby, Denmark

christian.damsgaard@cen.dtu.dk

Keywords: ETEM, NiGa alloys, *in situ* XRD

In an energy system based around decentralized hydrogen production, methanol synthesis under lower pressure conditions could be a way to store hydrogen on location. In the search of catalysts that might open up new process, conditions studies based on density functional theory (DFT) calculations have predicted a nickel gallium alloy to be active for this reaction [1]. NiGa catalysts prepared by incipient wetness impregnation on a high surface area silica support (Saint-Gobain NorPro), using a solution of nickel and gallium nitrates have shown very promising results [2]. This work presents detailed Environmental Transmission Electron Microscope (ETEM) investigations of synthesis of NiGa nanoparticles on a thin film support.

Samples were prepared by dissolving Ni(NO₃)₂ and Ga(NO₃)₃ in a Ni:Ga ratio of 5:3 in millipore water. The solution was subsequently dispersed on transmission electron microscope (TEM) sample grids. The sample grid was then mounted in a TEM heating holder and inserted in a FEI Titan ETEM with imaging C_s corrector as well as facilities for *in situ* gas reactions [3]. The ETEM was operated at 300 kV. The synthesis was performed *in situ* in a H₂ flow of 2 Nml/min at a pressure of 130 Pa. The reaction was investigated from room temperature (RT) to 660°C by subsequently obtaining bright field TEM images, diffraction patterns (DP), High Resolution TEM (HRTEM) images, and Electron Energy Loss Spectroscopy (EELS) data.

Figure 1 shows bright field images of the sample during synthesis. The dispersed nitrate salts (A) starts to decompose around 300 °C (B). From 400 °C to 660°C (C) NiGa nanoparticles are formed. The particle diameter at 660°C was between 5 nm and 20 nm. From HRTEM and DP it is observed that the nanoparticles are crystalline.

Figure 2(A) shows a particle at 660°C with two overlapping crystal domains. The insets show the fast fourier transform (FFT) of the overlapping crystals (FFT1) and single crystal area (FFT2), respectively. The FFT2 resembles the orthorhombic Ni₅Ga₃ viewed along the [1 1 -4] zone axis [4]. Figure 2(B) shows EELS of a single particle at 660°C. Both Ni and Ga edges are observed in the spectra. Quantification of Ni:Ga ratio is hampered by the presence of the Ni L₁ edge.

The ETEM experiments have been supported by complementary *in situ* X-Ray Diffraction (XRD) measurements on synthesis of Ni₅Ga₃ catalyst on a high surface area silica support prepared by wet impregnation [2]. Although the *in situ* XRD was performed at significantly higher H₂ flow (40 Nml/min) and pressure (100 kPa) the complimentary data correlates with the main temperature dependence of phase and structure and shows formation of the Ni₅Ga₃ phase for temperatures higher than 300°C.

1. F. Studt, F. Abild-Pedersen, J.K. Nørskov, SLAC, Stanford University (to be published).
2. I. Sharafutdinov et al., Technical University of Denmark (to be published).
3. T.W. Hansen, J.B. Wagner, and R.E. Dunin-Borkowski, *Materials Science and Technology* **11** (2010), p. 1338.
4. S. Bhan and K. Schubert, *Journal of the Less-Common Metals* **17** (1969), p. 73.
5. We kindly acknowledge the support from the Danish Ministry of Science and Innovation through the Catalysis for Sustainable Energy Initiative (CASE) at DTU and by The Danish National Research Foundation through CINF DTU. Furthermore, the A. P. Møller and Chastine Mc-Kinney Møller Foundation is gratefully acknowledged for its contribution towards the establishment of the Center for Electron Nanoscopy in the Technical University of Denmark.

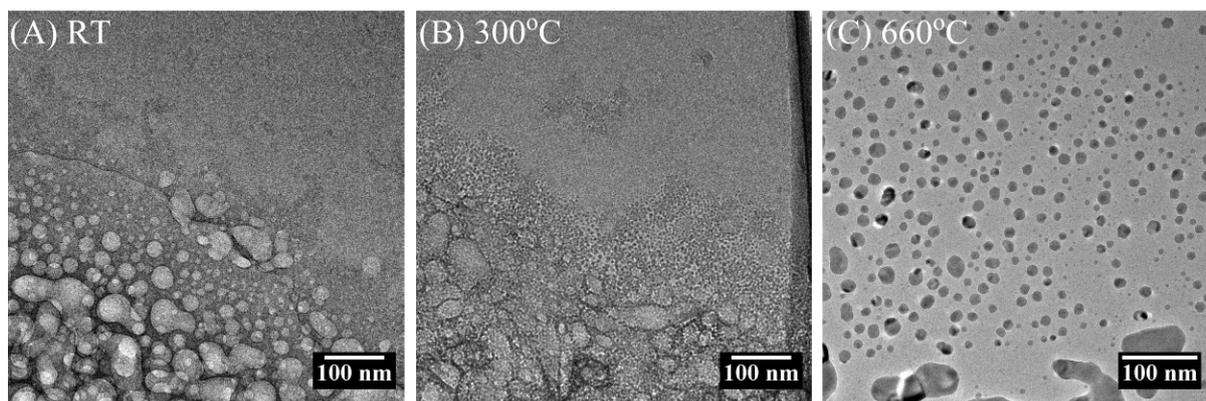


Figure 1. Bright field images of the sample during *in situ* synthesis in a H_2 flow of 2 Nml/min at a pressure of 130 Pa.

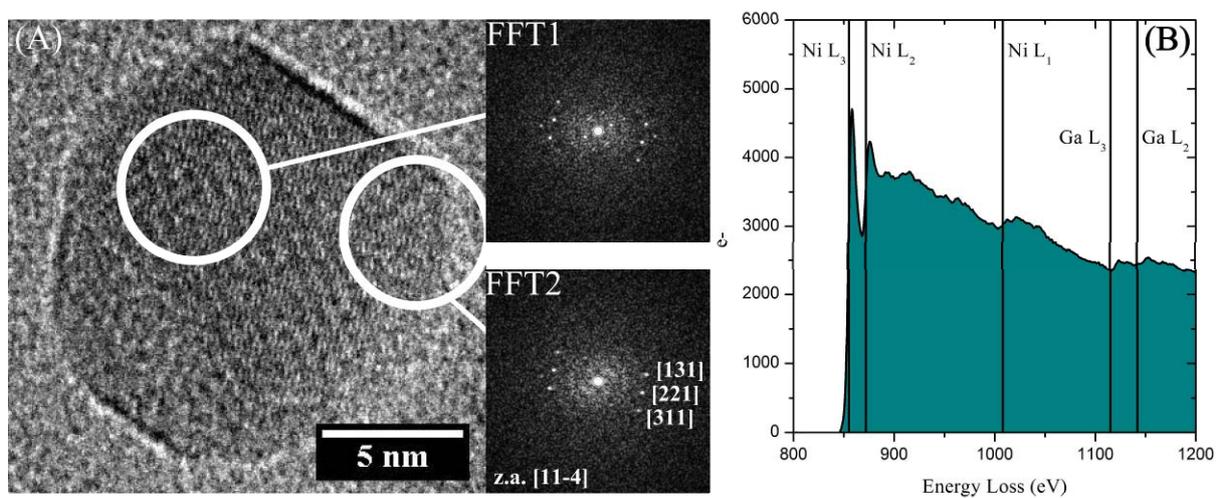


Figure 2. shows HRTEM image (A) and EELS (B) of a NiGa nanoparticle at 660°C in a H_2 flow of 2 Nml/min and at a pressure of 130 Pa. The insets in (A) show the FFT of two different parts of the particle (FFT2 zone axis [11-4]). The lines in (B) indicate Ni and Ga energy-loss edges.