



Electron beam-induced charging and modifications of thin films

Beleggia, Marco; Malac, M.; Rowan, T.; Egerton, R.; Kawasaki, M.; Okura, Y.; McLeod, R.

Published in:
Proceedings of Microscopy and Microanalysis 2015

Publication date:
2015

Document Version
Peer reviewed version

[Link back to DTU Orbit](#)

Citation (APA):
Beleggia, M., Malac, M., Rowan, T., Egerton, R., Kawasaki, M., Okura, Y., & McLeod, R. (2015). Electron beam-induced charging and modifications of thin films. In *Proceedings of Microscopy and Microanalysis 2015*

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Electron beam-induced charging and modifications of thin films.

Marek Malac^{△°}, Marco Beleggia[■], Teddy Rowan^{△#}, Ray Egerton^{△°}, Masahiro Kawasaki*, Yoshio Okura*, Robb McLeod^x

[△] National Institute of Nanotechnology, 11421 Saskatchewan Drive, Edmonton, Canada.

[°] Department of Physics, University of Alberta, T6G 2E1, Edmonton, Canada.

[#] University of British Columbia. 2329 West Mall, Vancouver, BC. V6T 1Z4

* JEOL Ltd. 1-2 Musashino- 3 chome, Akishima, Tokyo 198-8558, Japan.

[■] Centre of Electron Nanoscopy, Denmark Technical University, Denmark.

^x Fondation Nanosciences, 23 rue des Martyrs, 38000 Grenoble, France.

A thin film irradiated by high energy primary electrons (PE) emits secondary electrons (SE). The SE are emitted to the outside of the sample ($SE\alpha$) and within the plane of the sample ($SE\beta$) [1]. Figure 1 illustrates the various types of SEs. The PEs, $SE\alpha$ and the $SE\beta$ affect, by modifying the film properties, the rate at which the irradiated sample area tends toward a steady state. Both PE and $SE\beta$ can cause radiation damage [2] and electron beam induced conductivity (EBIC) [1]. The discussed phenomena are relevant to sample charging, damage and to various implementations of hole-free phase plate (HFPP) [3, 4]. The beam-induced modifications can result in a surface potential $\sigma(r)$ and in an electric field $E_V(r,z)$ in the vacuum near the sample [3].

An irradiated thin film tends toward a steady state, as measured by time dependence of $SE\alpha$ current and the evolution of the contrast transfer function (CTF) [3,4]. Figure 2 shows $SE\alpha$ signal (a) and, (b), the position of extrema in a CTF as a function of time. Both $SE\alpha$ and CTF time evolution can be fitted to:

$$Y(t) = Y_0 + A_0 \exp(-t/t_0) \quad \text{Eq. (1)}$$

Here $Y(t)$ and Y_0 are the dependent variable ($SE\alpha$ signal or CTF extrema position) and their initial values respectively. The time dependence ($Y(t)$) is exponential with a characteristic time t_0 . The Eq (1) allows define a settling time t_0 . The values of t_0 obtained from $SE\alpha$ and CTF closely correlate; they are a few tens of seconds for all studied materials. According to Eq. (1), the film state is within 2% of its asymptotic steady state after $t_s = 4t_0$. A steady state is achieved when a balance is reached between the $SE\alpha$ leaving the sample and the current from ground electrode I_G . At steady state, the electric field outside sample $E_V(r,z)$ reduces the $SE\alpha$ until it is fully compensated by the I_G . When multiple processes control the settling the Eq. (1) includes more than one term. The settling time t_s is then determined by the slowest process. The $A_0 > 0$ for $SE\alpha$ decay and for Thon rings that decrease diameter with time (i.e. the defocus and charging term in a CTF contribute phase shift with the same sign). The $A_0 < 0$ for Thon rings when defocus and charging contribute opposite sign of phase shift.

The irradiated area appears to remain close to the steady state after the PE beam is switched off [3,4,5]. This can be explained by existence of a charge-trapping layer on the film surface with electron tunneling governing the recombination charge transport. At steady state, the emitted $SE\alpha$ current density $j_{SE}(r)$ equals to a tunneling current $j_T(r)$ at every location r of the film, as graphically depicted in Figure 3 for Fowler-Nordheim (FN) and Poole-Frenkel (PF) tunneling mechanisms. The tunneling current exponentially depends on electric field $E_T(r,z)$ inside the

charge trapping layer which is related to the $j_{SE}(r)$. When the PE irradiation ceases and the $j_{SE}(r)$ goes to zero, an exponentially small decrease in $E_T(r,z)$ switches off the $j_T(r)$ effectively maintaining the steady state charge distribution. Figure 3 indicates that both FN and PF achieve steady state for realistic surface potential values.

The SE α escape depth δ is an important parameter in models capturing the behavior of irradiated films. Figure 4 shows the dependence of SE α signal and sample thickness for an *in-situ* drilled carbon film at 600°C. Because the SE α escape from both surfaces, the δ appears to be less than $\frac{1}{2}$ (6.8 nm) = 3.4 nm or ~ 20 atomic layers. Since escape depth is large in insulators and small in conductors [1], amorphous carbon at $T = 600^\circ\text{C}$ behaves as a good conductor.

The relative importance of EBIC, SE α emission and charge tunneling $j_T(r)$ is determined by mobility of charge carriers in the film, PE current density, by SE yield and its dependence on bias and thickness and dielectric properties of any surface layers on the film including contamination. The contribution of SE β to EBIC generation is small compared to PE [2].

[1] L. Reimer, Scanning Electron Microscopy 2nd ed., Springer, 1998.
 [2] RF Egerton, M Malac Microscopy and Microanalysis 10 (S02) (2004), p.1382.
 [3] M. Malac et. al., Ultramicroscopy 118 (2012), p. 77.
 [4] R. Danev et. al. PNAS, 111 (2015), p. 15635.
 [5] J. Berriman and K. L. Leonard, Ultramicroscopy 19 (1986), p. 349.
 [6] Support of NINT, NSERC, JEOL USA Inc. and JEOL Ltd. is gratefully acknowledged.

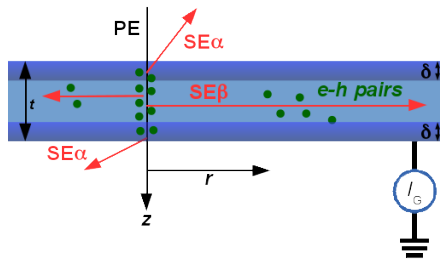


Fig. 1. Primary electrons (PE) incident on a thin film generates SE α that escape to vacuum from a depth δ , and SE β that travel within the specimen. The PE and SE β generate $e-h$ pairs that affect sample conductivity.

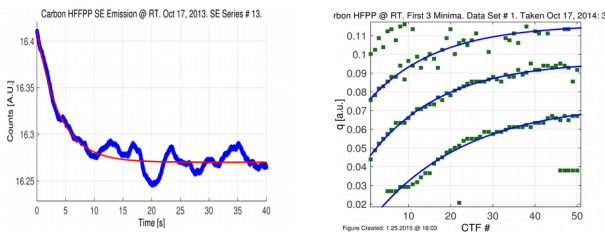


Fig. 2. Time traces of SE α current and CTF extrema from a 15 nm thick carbon film at room temperature and PE beam current density $j_{PE} = 0.1 \text{ A/cm}^2$. Both the SE α time traces and the position of extrema in CTF obey an exponential decay in Eq. (1). **Fit params, X axis C/cm^2**

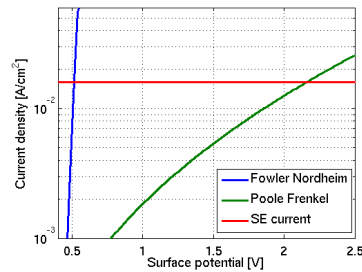


Fig. 3. At a steady state a balance between $j_{SE}(r)$ and $j_T(r)$ is maintained. An intersection of I-V curves corresponds to a balance. The FN tunneling (blue) has much steeper I-V dependence than the PF tunneling (green). The $j_{SE}(r)$ (red) is flat at typical values of surface potential.

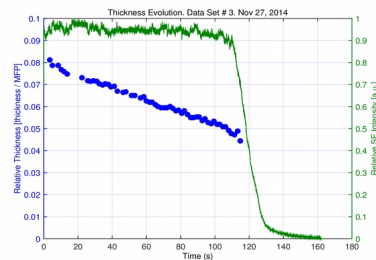


Fig. 4. SE α current and film thickness of an *in-situ* drilled carbon film at 600°C. A fast drop of SE α is observed at 6.5 nm thickness. The $j_{PE} = 0.6 \text{ A/cm}^2$.

