



## Advanced fabrication of hyperbolic metamaterials

**Shkondin, Evgeniy; Sukham, Johneph; Panah, Mohammad Esmail Aryaee; Takayama, Osamu; Malureanu, Radu; Jensen, Flemming; Lavrinenko, Andrei**

*Published in:*  
Proceedings of International Conference on Metamaterials and Nanophotonics, METANANO 2017

*Link to article, DOI:*  
[10.1063/1.4998025](https://doi.org/10.1063/1.4998025)

*Publication date:*  
2017

*Document Version*  
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

*Citation (APA):*  
Shkondin, E., Sukham, J., Panah, M. E. A., Takayama, O., Malureanu, R., Jensen, F., & Lavrinenko, A. (2017). Advanced fabrication of hyperbolic metamaterials. In *Proceedings of International Conference on Metamaterials and Nanophotonics, METANANO 2017* (Vol. 1874). [020004] American Institute of Physics Inc.. A I P Conference Proceedings Series Vol. 1874 <https://doi.org/10.1063/1.4998025>

---

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

## Advanced fabrication of hyperbolic metamaterials

Evgeniy Shkondin, Johneph Sukham, Mohammad E. Aryaee Panah, Osamu Takayama, Radu Malureanu, Flemming Jensen, and Andrei V. Lavrinenko

Citation: [AIP Conference Proceedings](#) **1874**, 020004 (2017); doi: 10.1063/1.4998025

View online: <http://dx.doi.org/10.1063/1.4998025>

View Table of Contents: <http://aip.scitation.org/toc/apc/1874/1>

Published by the [American Institute of Physics](#)

---

### Articles you may be interested in

[Race for novel high-index all-dielectric and hybrid metal-dielectric nanophotonic materials: Pit-stop optical tests](#)  
AIP Conference Proceedings **1874**, 020003 (2017); 10.1063/1.4998024

[Metamaterials for opto-acoustic interactions](#)  
AIP Conference Proceedings **1874**, 020006 (2017); 10.1063/1.4998027

[Effect of substrate on optical bound states in the continuum in 1D photonic structures](#)  
AIP Conference Proceedings **1874**, 030005 (2017); 10.1063/1.4998034

[Spatially-dispersive surface modes on interfaces of layered hyperbolic metamaterials](#)  
AIP Conference Proceedings **1874**, 040040 (2017); 10.1063/1.4998113

[Photonic quantum walks with symmetry protected topological phases](#)  
AIP Conference Proceedings **1874**, 020001 (2017); 10.1063/1.4998022

[In-situ fabrication of polymer/metal nanocomposite films using a mid-infrared laser](#)  
AIP Conference Proceedings **1874**, 020005 (2017); 10.1063/1.4998026

---

# Advanced Fabrication of Hyperbolic Metamaterials

Evgeniy Shkondin<sup>1</sup> and Johneph Sukham<sup>1</sup> and Mohammad E. Aryaee Panah<sup>1</sup> and Osamu Takayama<sup>1</sup> and Radu Malureanu<sup>1</sup> and Flemming Jensen<sup>2</sup> and Andrei V. Lavrinenko<sup>1, 3, a)</sup>

<sup>1</sup>*DTU Fotonik, Department of Photonics Engineering, Technical University of Denmark, Ørstedes Plads 343, DK-2800 Kgs. Lyngby, Denmark*

<sup>2</sup>*DTU Danchip—National Center for Micro- and Nanofabrication, Technical University of Denmark, Ørstedes Plads 347, DK-2800 Kgs. Lyngby, Denmark*

<sup>3</sup>*International Research Centre for Nanophotonics and Metamaterials, ITMO University, St. Petersburg, Russia.*

<sup>a)</sup> [alav@fotonik.dtu.dk](mailto:alav@fotonik.dtu.dk)

**Abstract.** Hyperbolic metamaterials can provide unprecedented properties in accommodation of high-k (high wave vector) waves and enhancement of the optical density of states. To reach such performance the metamaterials have to be fabricated with as small imperfections as possible. Here we report on our advances in two approaches in fabrication of optical metamaterials. We deposit ultrathin ultrasmooth gold layers with the assistance of organic material (APTMS) adhesion layer. The technology supports the stacking of such layers in a multiperiod construction with alumina spacers between gold films, which is expected to exhibit hyperbolic properties in the visible range. As the second approach we apply the atomic layer deposition technique to arrange vertical alignment of layers or pillars of heavily doped ZnO or TiN, which enables us to produce hyperbolic metamaterials for the near- and mid-infrared ranges.

## FABRICATION OF HYPERBOLIC METAMATERIALS

Typically hyperbolic metamaterials are presented by a layered multi-periodic media or by a bundle of nanopillars or nanowires [1,2]. The alteration of conducting (for example, metals, transparent conducting oxides or heavily doped semiconductors) and dielectric (air, oxides or high-resistive semiconductors below the bandgap) insertions should obey the principle condition for the homogenization legitimacy – it must happen on scales much smaller than the operating wavelength. Therefore, optical metamaterials, and hyperbolic metamaterials in particular, require extremely small thicknesses of the layers (down to 10 nm and even below) or lattice periods and diameters of the wires/pillars. Needless to say, that fabrication of the unitary elements must be accompanied with a very low roughness of the surfaces.

### Ultrathin Gold Layers

Gold is considered to be a backbone of plasmonics due to its conformal deposition, low material losses, inert behavior towards most of substances and open-air stability. So deposition of nanometers-thick gold films can be performed by sputtering techniques [3, 4] after a special preprocessing of the working surface with layers improving


adhesion of gold to the substrate. Conventionally the Ti or Cr adhesion layers are in use. However, when the thicknesses of the film become very small, the properties of the adhesion layer can deteriorate the overall performance of the structure towards, e.g. surface or bulk plasmon-polariton propagation or localized surface plasmons Q-factors [5].

We proposed to use 3-Aminopropyl-trimethoxy-silane (APTMS) as an adhesion layer for gold, obtaining an ultra-thin, ultra-smooth gold film of the thickness of 6 nm and roughness below 0.30 nm [3]. We prove the superior quality of the layers deposited by our approach (Fig.1a) by detection of excitation of short-range surface plasmon polaritons. As a reference we use layers deposited with the Cr-adhesion or without any adhesion layer. As a next step in advancing technology we report on stacking of few periods of gold-dielectric bi-layers to deliver a high-quality hyperbolic metamaterial prototype.

## Metamaterials with Vertically Arranged Elements

Another principal geometry that supports hyperbolic behavior is the so-called wire medium, e.g. an anisotropic composite of metallic pillars incorporated in a dielectric host matrix. Its one-dimensional analogue – trenched structure – can also exhibit specific hyperbolic dispersion of surface waves. Unfortunately, sputtering of gold cannot be used in fabrication neither of vertically standing nanopillars, nor vertical layers when even a moderate aspect ratio of unitary elements is required. The processing of such metamaterials can be done by atomic layer deposition (ALD), but gold then must be substituted by alternative plasmonic materials, which allow ALD processing, for example, aluminum doped ZnO [6,7].

We report on fabrication of extended arrays of AZO nanotrenches and nanopillars, which can be considered as metamaterials, in particular, hyperbolic metamaterials in mid-IR. Such choice is regulated by the period size, which is 400-500 nm due to limitations of the deep-UV laser lithography (Fig.1b).

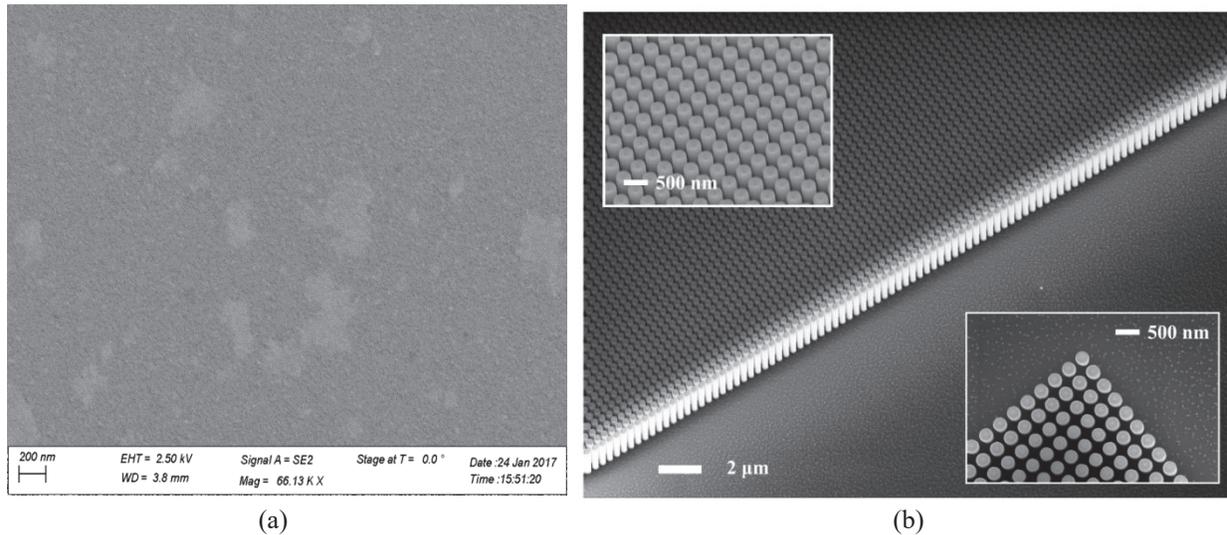

**FIGURE 1.** (a) 8 nm thick gold film deposited on APTMS adhesion layer; (b) Figure shows the bird-eye SEM image of finally prepared pillars, the insets shows the magnified image of pillars (top left) and top view of the array corner (bottom left).

Rather surprisingly, the tensor of the effective permittivity restored from the mid-IR reflectance spectra has a very strong anisotropy, but is positively defined. This astonishing discrepancy implies that AZO, once being confined in the nanopillar dimensions, becomes poor plasmonic material, and its permittivity significantly deviated from that of the flat film. So, this challenging fact poses a question of applicability of ALD deposited materials for hyperbolic metamaterials and definitely requires further attention.

## ACKNOWLEDGMENTS

This work (development of the technology) was supported by Villum Fonden “DarkSILD project No. 11116”, Denmark, and, partially, by Russian Science Foundation, grant #15-12-20028 (numerical simulations of hyperbolic metamaterials, AVL contribution).

## REFERENCES

1. A. Poddubny, *et al.*, [Nature Photonics](#), **7**, 958-967 (2013).
2. L. Ferrari, *et al.*, [Progress Quant. Electron.](#) **40**, 1-40 (2015).
3. L. Leandro, *et al.*, [ACS Appl. Mater. Interfaces](#) **7**, 5797–5802 (2015).
4. H. Qian, Y. Xiao, and Z. Liu, [Nat. Commun.](#) **7**, 13153 (2016).
5. T. Desalegn, *et al.*, [Opt. Mat. Express](#), **7**, 73-84 (2017).
6. E. Shkondin, *et al.*, [Opt. Mat. Express](#) **7**, 1606–1627 (2017).
7. O Takayama, *et al.*, arXiv preprint, [arXiv:1704.06108](#) (2017).