



Lithium-Oxygen Batteries: At a Crossroads?

Vegge, Tejs; García Lastra, Juan Maria; Siegel, Donald Jason

Published in:
Current Opinion in Electrochemistry

Link to article, DOI:
[10.1016/j.coelec.2017.10.014](https://doi.org/10.1016/j.coelec.2017.10.014)

Publication date:
2017

Document Version
Peer reviewed version

[Link back to DTU Orbit](#)

Citation (APA):
Vegge, T., García Lastra, J. M., & Siegel, D. J. (2017). Lithium-Oxygen Batteries: At a Crossroads? *Current Opinion in Electrochemistry*, 6(1), 100-107. <https://doi.org/10.1016/j.coelec.2017.10.014>

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Manuscript Details

Manuscript number	COELEC_2017_106
Title	Lithium-Oxygen Batteries: At a Crossroads?
Short title	Lithium-Oxygen Batteries: At a Crossroads?
Article type	Review article

Abstract

In this current opinion, we critically review and discuss some of the most important recent findings in the field of rechargeable lithium-oxygen batteries. We discuss recent discoveries like the evolution of reactive singlet oxygen and the use of organic additives to bypass reactive LiO₂ reaction intermediates, and their possible implications on the potential for commercialization of lithium-oxygen batteries. Finally, we perform a critical assessment of lithium-superoxide batteries and the reversibility of lithium-hydroxide batteries.

Corresponding Author	Tejs Vegge
Corresponding Author's Institution	Technical University of Denmark
Order of Authors	Tejs Vegge, Juan Maria Garcia Lastra, Donald Siegel
Suggested reviewers	Alan C. Luntz, Kristina Edström

Submission Files Included in this PDF

File Name [File Type]

Li-O₂_current opinion_Vegge et al_highlights_20170707.docx [Highlights]

Li-O₂_current opinion_Vegge et al_graphical abstract_20170707.docx [Graphical Abstract]

Li-O₂_current opinion_Vegge et al_20170707_manuscript.docx [Manuscript File]


To view all the submission files, including those not included in the PDF, click on the manuscript title on your EVISE Homepage, then click 'Download zip file'.

Highlights

- Important recent developments in Li-O₂ batteries are highlighted
 - New additives can bypass the LiO₂ intermediate and promote solution phase formation of Li₂O₂ in weakly solvating electrolytes
 - The role of singlet oxygen and its implications for electrolyte and electrode degradation
 - A critical assessment of lithium-superoxide batteries
 - Analyzing the reversibility of lithium-hydroxide batteries
 - Next-generation Li-O₂ electrolytes: Do solid and hybrid electrolytes hold the key?
-

Graphical abstract

Have lithium-oxygen batteries reached a crossroads? Will either of these approaches lead to the commercialization of secondary lithium-oxygen batteries?

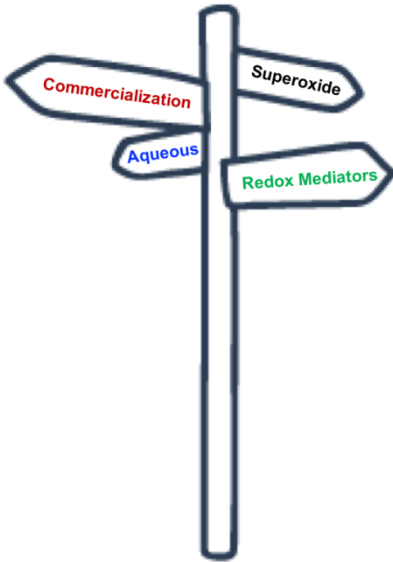

Lithium-Oxygen Batteries: At a Crossroads?

Tejs Vegge¹, Juan Maria Garcia-Lastra¹, and Donald J. Siegel²

Addresses

- 1) Department of Energy Conversion and Storage, Technical University of Denmark, Kgs. Lyngby, Denmark
- 2) Mechanical Engineering, Materials Science & Engineering, Applied Physics Program, and Michigan Energy Institute, University of Michigan, Ann Arbor, MI USA

Corresponding author: Vegge, Tejs (teve@dtu.dk)

Abstract

In this current opinion, we critically review and discuss some of the most important recent findings in the field of rechargeable lithium-oxygen batteries. We discuss recent discoveries like the evolution of reactive singlet oxygen and the use of organic additives to bypass reactive LiO_2 reaction intermediates, and their possible implications on the potential for commercialization of lithium-oxygen batteries. Finally, we perform a critical assessment of lithium-superoxide batteries and the reversibility of lithium-hydroxide batteries.

Introduction

Secondary lithium-oxygen (Li-O_2) batteries remain one of the most hotly pursued and hotly contested future technologies for electrochemical energy storage. Li-O_2 batteries offer an alluring theoretical specific energy ($\sim 3.500 \text{ Wh/kg}$) - nearly an order of magnitude greater than state-of-the-art in Li-ion batteries ($\sim 300 \text{ Wh/kg}$) - yet their practically accessible specific energy remains low.

Two decades after the first report by Abraham and Jiang,¹ and roughly a decade after its scientific light-off,^{2,3} more than 1.700 scientific articles have been published on the Li-O_2 system, with more than 57.000 citations.⁴ This publication activity appears to have peaked in 2015-2016, raising the question whether this 'peak Li-O_2 ' is a consequence of the fundamental mechanisms being fully understood (perhaps with commercialization imminent) or instead a sign of wavering interest from the community?

It is our opinion that neither of these viewpoints is entirely correct. Recent publications clearly document that breakthroughs in understanding and novel approaches to improve performance are still emerging at a rapid pace. At the same time, it is equally clear that near-term commercialization remains elusive. Here, we seek to highlight and review some of the most important recent Li-O_2 publications and discuss their potential impact on future research and development of secondary Li-O_2 batteries.

Fundamental Li-O_2 mechanisms

In discussing the current progress in the Li-O_2 field, a natural distinction is between aqueous and non-aqueous (aprotic) systems, where the latter has received the most attention due to its higher accessible energy density and greater likelihood for reversibility.⁵ Nevertheless, a recent publication from Grey *et al.* sparked renewed interest and debate in the aqueous system,⁶ as discussed below.

In the aprotic system, two distinctly different mechanisms for oxygen reduction can lead to the formation of the desired Li_2O_2 (peroxide) discharge product: (i.) a surface-based mechanism, where the LiO_2 (superoxide) reaction intermediate binds to the positive electrode surface or to previously deposited Li_2O_2 , and, (ii.) a solution-based mechanism, where the LiO_2 intermediate is dissolved in the electrolyte and disproportionates into insoluble Li_2O_2 particles/toroids and O_2 .⁷ Which of these mechanisms dominates depends on the relative stability of surface adsorbed LiO_2^* and LiO_2 in solution, where the latter has been

argued to depend on the Gutman acceptor (AN) and donor number (DN) of the electrolyte⁸ and the applied ORR potential.⁹ For detailed reviews of the different mechanisms in Li-O₂, we refer to Aurbach *et al.*¹⁰ and Kang *et al.*¹¹

The limitations of the surface-based mechanism are now well understood. For example, the fundamental overpotential for deposition of Li₂O₂ is very low (as originally predicted from density functional theory (DFT) calculations¹²), while the high charging potentials observed in early studies employing, e.g., carbonate-based electrolytes are due to parasitic chemistry.^{13,14} Independent of electrolyte composition, the insulating nature of the formed Li₂O₂ thin-films is the origin of the 'sudden death' during discharge.^{15,16,17} At ambient conditions and moderate current densities, the electronic conduction is dominated by tunneling of holes in the valence band of Li₂O₂,¹⁸ whereas hole polarons become important at higher temperatures and/or low current densities.^{19,20,21,22,23} However, neither mechanism appears capable of providing the electronic conductivity needed to decompose relatively thick Li₂O₂ deposits at moderate current densities and with low overpotentials.

Redox mediators and additives

In terms of maximizing discharge capacity, the solution-based mechanism easily surpasses the surface-based mechanism. This is possible because the solution mechanism allows the formation of large, micron-sized Li₂O₂ particles, typically with toroidal morphologies.⁷ However, the electrolytes and impurities that support this mechanism (e.g. water) also increase parasitic side reactions.²⁴ Also, Li₂O₂ particles formed via this mechanism may be located far from the electrode surface, resulting in very slow recharging, or worse, loss of electrical contact (i.e., Li₂O₂ stranded on the separator).

The use of redox mediators (RM) could circumvent slow charge transfer between 'distant' Li₂O₂ particles and the solid electrode surface. This approach has been investigated intensely since the first report from Bruce *et al.* on the use of the tetrathiafulvalene (TTF) RM.²⁵ Here, the (TTF/TTF⁺) redox couple facilitates chemical oxidation of Li₂O₂ by acting as a molecular electron-hole transfer agent between Li₂O₂ and the electrode surface.²⁶ A range of different redox mediators have now been investigated, including TEMPO,²⁷ TDPA,²⁸ cobaltocene, and ferrocene.^{29,8} Nevertheless, this approach has yet to lead to a major breakthrough, in part due to buildup of Li₂O₂ and other insulating decomposition products on the electrode surface, which blocks the oxidation of the RM at the electrode. Moreover, RMs often introduce side reactions that may limit performance and can contribute to erroneous conclusions regarding mechanisms. Multiple characterization techniques should therefore be invoked to fully understand their impact.³⁰

In an interesting recent publication, Bruce *et al.* showed that using a 2,5-di-*tert*-butyl-1,4-benzoquinone (DBBQ) electrolyte additive can promote solution phase formation of Li₂O₂ in low-polarity and weakly solvating electrolytes; thereby apparently dodging the double-edged sword of high capacity but poor stability of the high AN/DN solvents. Since DBBQ also suppresses the surface reduction to Li₂O₂, this leads to a capacity increase of up to two orders of magnitude.³¹ By utilizing a LiDBBQO₂ intermediate, Bruce *et al.* could bypass the LiO₂ intermediate in solution, leading to reduced overpotentials for charge and reduced electrolyte degradation resulting from parasitic side reactions (see Fig. 1). Although more work is needed to identify new additive-solvent combinations with improved cyclic performance, the approach shows promise.

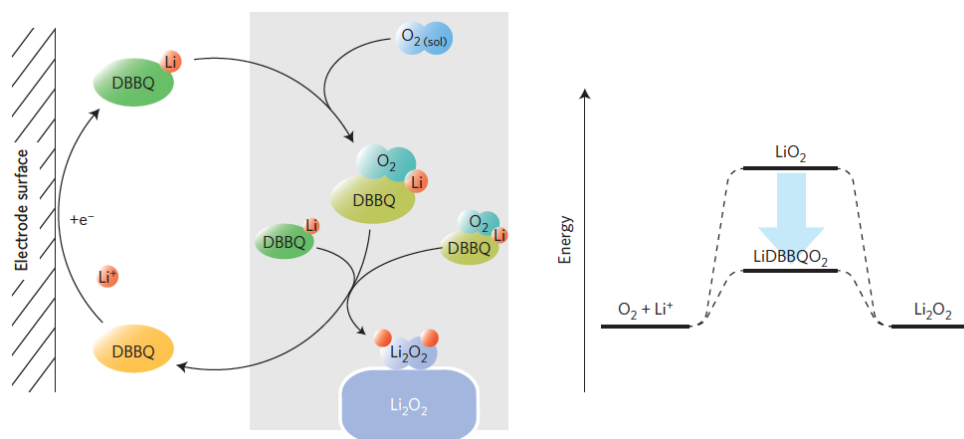


Fig. 1 Schematics of reactions on discharge (left) and the effect of DBBQ on the potential determining step (right). DBBQ is reduced at the electrode surface, forming LiDBBQ, and then LiDBBQ reacts with O_2 , producing Li_2O_2 and itself being regenerated to DBBQ. The schematic of the free-energy plot is at E^0 for O_2/Li_2O_2 . Reprinted with permission from Ref. 31. Copyright 2017 Nature Publishing Group.

Singlet oxygen

The aggressive nature of the strong nucleophiles and bases present in the Li- O_2 battery chemistry, *i.e.*, O_2^- , LiO_2 , $Li_{2-x}O_2$ and Li_2O_2 species, pose severe challenges for the stability of electrodes, solvents,³² and salts.³³ It has long been suspected that these reactive species are responsible for the majority of the parasitic reactions that preclude true reversibility, *i.e.* a perfect 1:1 mapping between the amount of O_2 consumed during discharge with that released during charge (see Fig. 2).^{34,35}

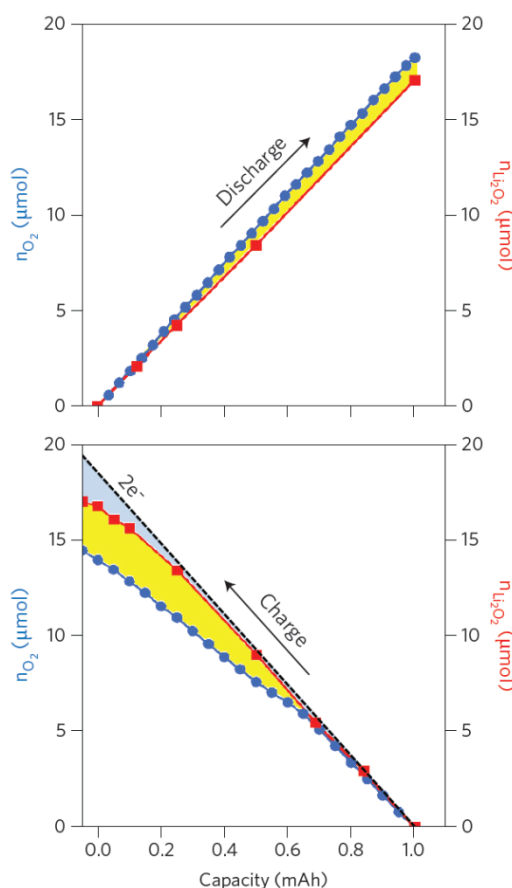


Fig. 2 Deviation from a truly reversible Li- O_2 electrochemistry. Top panel: number of moles of O_2 consumed (n_{O_2} , blue) and of Li_2O_2 formed ($n_{Li_2O_2}$, red) during a 1 mAh Li- O_2 discharge. The ideal line for two electrons per O_2 consumed is indistinguishable from the blue points. Bottom panel: number of moles of O_2 evolved (n_{O_2} , blue) and Li_2O_2 consumed ($n_{Li_2O_2}$, red) during recharge of

the battery above. The ideal line for $2e^-$ consumption reflects the total charging current. The region in yellow for both discharge and charge reflects the parasitic contribution that could arise from singlet oxygen ($^1\Delta_g$). The region in blue on charge is due to parasitic oxidation of species unrelated to Li_2O_2 and therefore presumably not related to singlet oxygen formation. Reprinted with permission from Ref. 35. Copyright 2017 Nature Publishing Group.

A recent discovery by Eichel *et al.*, showing that highly reactive singlet oxygen, $^1\text{O}_2$, is evolved upon Li_2O_2 oxidation at potentials above 3.5 V,³⁶ could change this perception. Eichel *et al.* demonstrated that singlet oxygen plays a crucial role in the electrolyte degradation and carbon corrosion during charging of the Li- O_2 cell. Freunberger *et al.* later documented that singlet oxygen is already produced at the onset of charge and can also be produced via the disproportionation of LiO_2 to Li_2O_2 and $^1\text{O}_2$, and that the amount of $^1\text{O}_2$ is enhanced in the presence of water impurities.³⁷ These interesting findings identify $^1\text{O}_2$ as a 'must solve' challenge to achieve reversible cycling by formation/decomposition of Li_2O_2 . This discovery opens new research directions in the search for new materials and approaches to improve the stability, e.g. the use of singlet oxygen traps, as discussed by Luntz and McCloskey.³⁴

Next-generation Li- O_2 electrolytes

Multiple strategies have been proposed to overcome limitations associated with electrolyte stability, including use of alternative electrolyte compositions employing ionic liquids (IL), polymers,³⁸ IL-polymer composites,³⁹ and hybrid solid-liquid electrolytes.^{40,41} Following the initial promise of ILs,^{42,43} subsequent differential electrochemical mass spectrometry (DEMS) studies showed that their stability was ultimately insufficient for practical applications.^{44,45} Using a nitrate-based molten salt electrolyte (*i.e.*, an eutectic mixture of LiNO_3 and KNO_3), Addison *et al.*, however, recently showed very low charge/discharge overpotentials and enhanced rate capability, due to improved stability and moderate solubility of Li_2O_2 in this electrolyte. Although promising, the observed capacity loss during cycling was still too high for practical applications.⁴⁶

The use of hybrid solid-liquid electrolytes and all-solid-state electrolytes is also being actively pursued.⁴⁷ In an interesting recent study, Luo *et al.* used *in situ* environmental transmission electron microscopy to study the Li- O_2 reaction mechanisms in a solid Li_2O electrolyte, yielding valuable insight about the formation and transient disproportionation of metastable LiO_2 in solid electrolytes.⁴⁸ Further progress in the field of solid-state electrolytes is needed, both in terms of increased solubility of the oxygen reduction species and improved electrolyte conductivity.⁴⁹ Substantial improvements are being made in the latter area, e.g., through use of garnet ceramic electrolytes like LLZO ($\text{Li}_7\text{La}_3\text{Zr}_2\text{O}_{12}$)^{50,51,52,53} and nano-structured composite electrolytes,⁵⁴ but further work is needed to improve performance during battery charging.

Lithium-superoxide batteries

Whereas the related Na- O_2 battery chemistry readily forms sodium superoxide (NaO_2) as the main discharge product,^{55,56} stable superoxide products have remained elusive in the Li- O_2 system. Contrary to the conventional behavior of Li- O_2 systems, Ammine *et al.* recently reported that cathodes based on reduced graphene oxide (rGO) with added iridium (Ir) nanoparticles yield LiO_2 as the main discharge product,⁵⁷ sparking massive interest. They observed the formation of large rod-like nanoparticles that were identified as LiO_2 based on DEMS, high-energy X-ray diffraction (HE-XRD), and Electron Paramagnetic Resonance (EPR) experiments. The DEMS experiments resulted in an e^-/O_2 ratio of 1.00 (1.02) during discharge (charge), which is the main fingerprint of the superoxide formation.⁵⁷ The HE-XRD data is compatible with the DFT-predicted LiO_2 crystalline marcasite structure⁵⁸ (no XRD data of LiO_2 has previously been reported, as it is an unstable compound). The EPR signal exhibits a peak at $g = 2.1019$, consistent with the presence of superoxide ions (peroxide ions are silent in EPR).

Ammine *et al.* suggests a complex route for the formation of the LiO_2 nanorods: first, the Ir nanoparticles alloy with Li-ions to give rise to Ir_3Li nanoparticles; second, LiO_2 nanorods grow epitaxially on top of the Ir_3Li substrate. The large size of the nanorods is explained through DFT calculations at the Generalized Gradient

Approximation (GGA) level, which showed that LiO_2 is a half-metal, allowing the long-range transport of electrons required for the reaction.⁵⁷ The metallic nature of LiO_2 is, however, still an open question, since other authors have found non-zero bandgaps of 3.6⁵⁹-3.7⁶⁰ eV for LiO_2 (and 5.3 eV for NaO_2 ⁶¹), using higher level theory. Similarly, the measured electrical conductivity of other alkali metal superoxides (KO_2 , RbO_2 , and CsO_2) is poor.⁶²

The proposed formation of Ir_3Li nanoparticles is not straightforward from a thermodynamic point of view. The enthalpy of alloying per Ir atom in Ir_3Li has been calculated as -0.4 eV,⁶³ which is low compared to the experimental enthalpy of formation of rutile IrO_2 , -2.6 eV per Ir atom.⁶⁴ Amorphous IrO_x compounds have also been reported to be very stable.⁶⁵ Thus, it seems plausible that oxidation of the Ir nanoparticles could occur at the expense of alloying of Ir and Li.

Once $\text{IrO}_2/\text{IrO}_x$ nanoparticles are formed, the subsequent formation of Li_2IrO_3 nanostructures is conceivable. Indeed, studies by Tarascon *et al.*^{66,67} on the electrochemical performance of $\alpha\text{-Li}_2\text{IrO}_3$ and $\beta\text{-Li}_2\text{IrO}_3$ polymorphs provide an alternative interpretation of the results reported by Ammine *et al.* Early studies showed that $\alpha\text{-Li}_2\text{IrO}_3$ displays some peculiarities with respect to related layered materials. First, $\alpha\text{-Li}_2\text{IrO}_3$ is metallic⁶⁸ (rutile IrO_2 and amorphous IrO_x are also metallic⁶⁵), which would be compatible with the observation of large nanorods in the experiments from Ammine *et al.* $\alpha\text{-Li}_2\text{IrO}_3$ decomposes into Li, IrO_2 and O_2 at a relatively low temperature (450 K),⁶⁸ which points towards low kinetic barriers for its formation. Furthermore, $\alpha\text{-Li}_2\text{IrO}_3$ can be electrochemically delithiated to $\text{Li}_{0.5}\text{IrO}_3$.^{66,69} Finally, Tarascon *et al.* have shown that the oxidation/reduction of $\alpha\text{-Li}_2\text{IrO}_3$ is very flexible, in the sense that it can happen either at the cations (Ir^{4+} to Ir^{5+}) or at the anions (2-O^{2-} to peroxy-like O_2^{3-}), which are active in EPR experiments.⁶⁶ This last property is shared by the $\beta\text{-Li}_2\text{IrO}_3$ polymorphs, which can be electrochemically delithiated to give rise to IrO_3 .⁶⁷ These considerations suggests that a reversible $x\cdot(\text{Li}^+\text{e}^+\text{O}_2) + \text{IrO}_y \rightarrow \text{Li}_x\text{IrO}_3$ reaction pathway is also compatible with the DEMS, EPR and HE-XRD measurements (see Fig. 3).

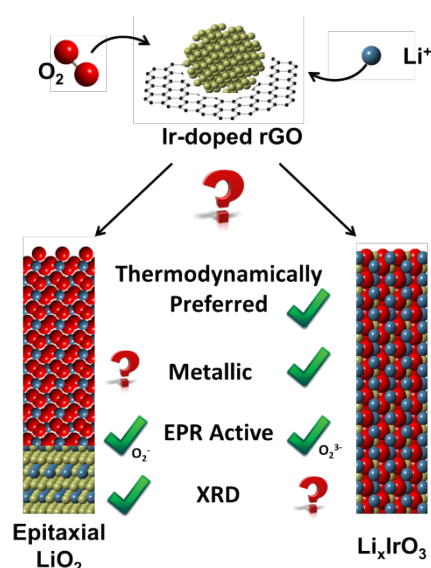


Fig. 3 Two possible interpretations of the experiments by Ammine *et al.* using a reduced Graphene oxide (rGo) doped with iridium nanoparticles as a cathode in Li-O_2 batteries. On the left, the original interpretation by Ammine *et al.*, in which epitaxial lithium superoxide nanorods on Ir_3Li alloy nanoparticles were hypothesized. On the right, an alternative interpretation based on the formation of lithium iridate particles. In the middle, the experimental properties which are compatible with each the two interpretations (a question mark means that the compatibility of an experimental property with the corresponding interpretation needs to be investigated).

Aqueous lithium-oxygen batteries

In contrast to the well-studied non-aqueous Li-O_2 cell, where the discharge product is solid Li_2O_2 , Liu *et al.* recently demonstrated a system that reversibly cycled LiOH .⁶ Other factors being equal, the formation of LiOH as the discharge product is advantageous, as it is more stable than Li_2O_2 , and may therefore suppress parasitic side reactions. The LiOH cell comprised a macroporous rGO positive electrode, and a DME-based


electrolyte containing water and LiI. In addition to eliminating reactive Li_2O_2 , the LiOH-based cell exhibited extremely high capacities ($>20,000 \text{ mAh/g}_{\text{carbon}}$) and a discharge-charge voltage hysteresis as low as 0.2 V, corresponding to a round-trip efficiency of 93.2%. The formation of LiOH was claimed to occur via an unusual 4-electron process involving the consumption of water additives in the electrolyte:



This remarkable performance was attributed to several of factors. First, the LiI additions provide redox mediation through the reaction



Here, I^- is oxidized near the observed charging voltage of 3 V. The resulting I_3^- was proposed to chemically decompose LiOH to water and oxygen gas:



Second, the presence of H_2O and LiI induce the growth of relatively large LiOH particles, contributing to the large observed capacity. Finally, the macroporous rGO support also contributes to the formation of large LiOH particles (tens of microns in diameter), while allowing for rapid diffusion of redox active species.

Liu *et al.*'s report of a reversible LiOH battery has sparked vigorous debate. For example, a pair of Technical Comments^{70,71} questioned the possibility of chemical decomposition of LiOH by I_3^- , via reaction (c), which is uphill in free energy and will thus not occur spontaneously, as suggested. This apparent discrepancy is reflected in the more positive equilibrium voltage of reaction (a), 3.4 V under standard conditions, compared to that of reaction (b), 3.0 V. (This voltage trend is the opposite of what is expected for a viable redox mediator, whose redox potential should slightly more positive than that of reaction (a) being mediated). In their response, Liu *et al.* argued that the non-standard chemical environment of their cell could reduce the voltage of reaction (a) to be closer to the 3.0 V needed for oxidation of I^- . Nevertheless, Liu *et al.* cautioned that "the equilibria that occur in the presence of oxygen, water, and iodine are complex..." and "...further mechanistic studies are required to understand the role of these complex equilibria in the redox processes."^{72,73}

More recently, Burke *et al.* confirmed the 4-electron process resulting in LiOH formation proposed by Liu *et al.* (reaction (a)) in a cell containing LiI and H_2O .⁷⁴ However, Burke *et al.* were unable to corroborate the charging mechanism proposed by Liu *et al.* Rather, LiOH was observed to decompose at 3.5 V or higher, which is 0.5 V more positive than in Ref. [6] (see Fig. 4). This higher voltage window was observed to coincide with operation of the I_3^-/I_2 couple, and not that of reaction (b). Importantly, LiOH decomposition resulted in the formation of soluble LiIO_3 , but not O_2 evolution, suggesting that the cell is, unfortunately, not truly reversible. Nevertheless, Burke *et al.* concluded that the electrochemistry in cells with different cathode supports, additives, and electrolyte components should exhibit different, and possibly more promising, behavior. Thus, ample opportunities exist to further explore the composition space of this complex system.

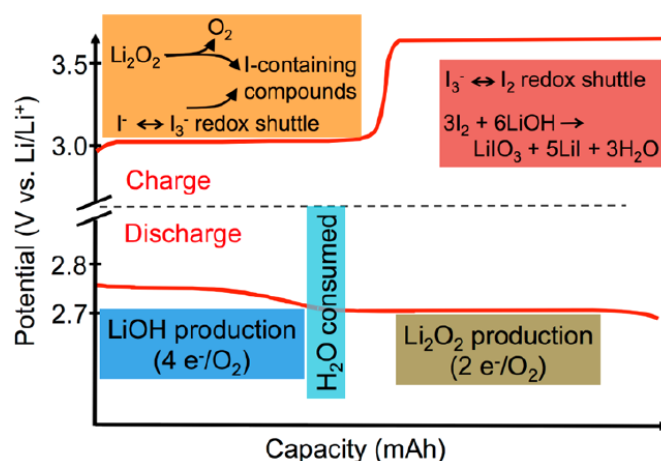


Fig. 4 Schematic of the mechanisms associated with discharge and charging of a Li/O₂ cell with LiI and H₂O additives Reprinted with permission from Ref. 74. Copyright 2016 American Chemical Society.

Summary

Although the fundamental mechanisms in the Li-O₂ battery chemistry are becoming increasingly well understood, new insights, interesting concepts, and new challenges continue to emerge. Therefore, we have not yet arrived at the crossroads between commercialization and abandonment.

Several new ideas in the Li-O₂ system have recently emerged, warranting additional research, e.g. the use additives such as BDDQ, which can help bypass the LiO₂ intermediate and thereby enable more stable electrolytes like ethers with low DN and combine to yield higher rates, capacity and cycle-life. It is, however, imperative that when new redox mediators or additives are introduced, careful quantitative analysis and characterization is performed using complementary techniques, as the true origin of a new mechanism may well be hidden under the surface.

An improved understanding of the complexity of the decomposition reactions during charging is still needed. This includes clarifying the exact conditions for generation and suppression of singlet oxygen, and the identification of suitable quenching agents with a sufficiently high electrochemical stability window. These questions appear far more vital than continued investigations of ORR/OER catalysts, which in our opinion have been overemphasized.

Finally, solid or hybrid electrolytes could hold the key to the development of more stable electrolytes strategies, but research for these materials is in its infancy, with many fundamental questions still to be answered.

Acknowledgements

The authors would like to acknowledge financial support from the ReLiab project (project no. 11-116792) funded by the Danish Council for Strategic Research, Program Commission on Sustainable Energy and Environment, and the Villum Foundation's Young Investigator Programme through the Mat4Bat project (grant number 10096). D.J.S. acknowledges DTU Energy, the Villum Foundation's Visiting Professor Program, and the Nordea Foundation's Residence Program for support during his stay at DTU. Financial support for work performed at the University of Michigan was provided by the National Science Foundation, grant CBET-1351482.

References and recommended reading

¹ K. Abraham and Z. Jiang, **A polymer electrolyte-based rechargeable lithium/oxygen battery**, *J. Elec. Soc.*, 143 (1996), pp. 1-5

-
- ² T. Kuboki, T. Okuyama, T. Ohsaki, N. Takami, **Lithium-air batteries using hydrophobic room temperature ionic liquid electrolyte**, *J. Power Sources*, 146 (2005), pp. 766–769
- ³ J. Read, **Ether-Based Electrolytes for the Lithium/Oxygen Organic Electrolyte Battery**, *J. Elec. Soc.*, 153 (2006), A96
- ⁴ Web of Science search: Title= “Li-O₂ or Lithium-air or Li-oxygen or Lithium-O₂ or Li-O-2 or Li-air or Lithium-oxygen or lithium superoxide or lithium peroxide” (Date: 2017-07-05).
- ⁵ J. Lu, L. Li, J.-B. Park, Y.-K. Sun, F. Wu and K. Amine, **Aprotic and Aqueous Li-O₂ Batteries**, *Chem. Rev.* 114, (2014), pp. 5611-5640
- ⁶ T. Liu, G. Kim, J. Carretero-González, E. Castillo-Martínez, C. P. Grey, **Cycling Li-O₂ batteries via LiOH formation and decomposition**, *Science*, 350 (2016), pp. 530-533
- ** Reports on a high reversible cycling capacity for Li-O₂ by use of LiI additives and H₂O.
- ⁷ N. B. Aetukuri, B. D. McCloskey, J. M. García, L. E. Krupp, V. Viswanathan and Alan C. Luntz, **Solvating additives drive solution-mediated electrochemistry and enhance toroid growth in non-aqueous Li-O₂ batteries**, *Nature Chem.*, 7 (2015), pp. 50-56
- ⁸ K. B. Knudsen, J. E. Nichols, T. Vegge, A. C. Luntz, B. D. McCloskey, J. Hjelm, **An Electrochemical Impedance Spectroscopy Study on the Effects of the Surface- and Solution-Based Mechanisms in Li-O₂ Cells**, *J. Electrochem. Soc.*, 9 (2016), pp. A2065-A2071
- ⁹ D. G. Kwabi, M. Tułodziecki, N. Pour, D. M. Itkis, C. V. Thompson, and Y. Shao-Horn, Controlling Solution-Mediated Reaction Mechanisms of Oxygen Reduction Using Potential and Solvent for Aprotic Lithium–Oxygen Batteries, *J. Phys. Chem. Lett.*, 7 (2016), pp. 1204–1212
- * Documents the significance of the applied potential on the ratio of the surface to solution-based mechanisms.
- ¹⁰ D. Aurbach, B. D. McCloskey, L. F. Nazar and P. G. Bruce, **Advances in understanding mechanisms underpinning lithium–air batteries**, *Nature Energy*, 1 (2016), pp. 1-11
- ¹¹ H.-D. Lim, B. Lee, Y. Bae, H. Park, Y. Ko, H. Kim, J. Kim and K. Kang, **Reaction chemistry in rechargeable Li-O₂ batteries**, *Chem. Soc. Rev.*, 46 (2017), pp. 2873-2888
- ¹² J. S. Hummelshøj, J. Blomqvist, S. Datta, T. Vegge, J. Rossmeisl, K. Thygesen, A. C. Luntz, K. W. Jacobsen, J. K. Nørskov, **Communication: Elementary oxygen electrode reactions in the aprotic Li-air battery**, *J. Chem. Phys.*, 132 (2010), 071101
- ¹³ J. Højberg, K. Knudsen, J. Hjelm, T. Vegge, **Reactions and SEI formation during charging of Li-O₂ cells**, *ECS Electrochem. Lett.*, 4 (2015), pp. A63-A66
- ¹⁴ J. Højberg, B. D. McCloskey, J. Hjelm, T. Vegge, K. Johansen, P. Norby, A. C. Luntz, **An Electrochemical Impedance Spectroscopy Investigation of the Overpotentials in Li-O₂ Batteries**, *ACS Appl. Mater. Interfaces*, 7 (2015), pp. 4039-4047
- ¹⁵ V. Viswanathan, K. S. Thygesen, J. S. Hummelshøj, J. K. Nørskov, G. Girishkumar, B. D. McCloskey, and A. C. Luntz, **Electrical conductivity in Li₂O₂ and its role in determining capacity limitations in non-aqueous Li-O₂ batteries**, *J. Phys. Chem.*, 135 (2011), 214704
- ¹⁶ J. Chen, J.S. Hummelshøj, K.S. Thygesen, J.S.G. Myrdal, J. K. Nørskov, T. Vegge, **The role of transition metals interfaces on the electronic transport in lithium-air batteries**, *Catalysis Today*, 165 (2011), pp. 2-9
- ¹⁷ M. D. Radin, C. W. Monroe, and D. J. Siegel, **Impact of Space Charge Layers on Sudden Death in Li/O₂ Batteries**, *J. Phys. Chem. Lett.*, 6 (2015), 3017
-

-
- ¹⁸ V. Viswanathan, J. K. Nørskov, A. Speidel, R. Scheffler, S. Gowda, and A. C. Luntz, **Li-O₂ Kinetic Overpotentials: Tafel Plots from Experiment and First-Principles Theory**, *J. Phys. Chem. Lett.*, 4 (2013), pp. 556-560
- ¹⁹ J. M.G. Lastra, J.S.G. Myrdal, R. Christensen, K. S. Thygesen and T. Vegge, **DFT+U study of polaronic conduction in Li₂O₂ and Li₂CO₃: Implications for Li-air batteries**, *J. Phys. Chem. C*, 117 (2013), pp. 5568-5577
- ²⁰ M. D. Radin, F. Tian, and D. J. Siegel, **Electronic Structure of Li₂O₂ (0001) Surfaces**. *J. Mater. Sci.*, 47 (2012), 7564
- ²¹ M. D. Radin and D. J. Siegel, **Charge Transport in Lithium Peroxide: Relevance for Rechargeable Metal-Air Batteries**, *Energy & Environ. Science* 6 (2013), 2370
- ²² F. Tian, M. D. Radin, and D. J. Siegel, **Enhanced Charge Transport in Amorphous Li₂O₂**, *Chem. Mater.*, 26 (2014), 2952
- ²³ Y. Mekkonen, J. M. Garcia-Lastra, J. S. Hummelshøj, J. Chengjun, T. Vegge, **The Role of Li₂O₂@Li₂CO₃ Interfaces on Charge Transport in Non-Aqueous Li-Air Batteries**, *J. Phys. Chem. C*, 119 (2015), pp. 18066-18073
- ²⁴ R. Younesi, P. Norby, T. Vegge, **A New Look at the Stability of Dimethyl Sulfoxide and Acetonitrile in Li-O₂ Batteries**, *ECS Electrochem. Lett.*, 3 (2014), pp. A15-A18
- ²⁵ G. V. Chase, et al., **Soluble oxygen evolving catalysts for rechargeable metal-air batteries**. US patent US20120028137 A1 (2012)
- ²⁶ Y. Chen, S. A. Freunberger, Z. Peng, O. Fontaine and P. G. Bruce, **Charging a Li-O₂ battery using a redox mediator**, *Nature Chem.*, 5 (2013), pp. 489-494
- ²⁷ B. J. Bergner, A. Schürmann, K. Peppler, A. Garsuch and J. Janek, **TEMPO: a mobile catalyst for rechargeable Li-O₂ batteries**, *J. Am. Chem. Soc.*, 136 (2014), pp. 15054-15064
- ²⁸ D. Kundu, R. Black, B. Adams and L. F. Nazar, **A highly active low voltage redox mediator for enhanced rechargeability of lithium-oxygen batteries**, *ACS Cent. Sci.*, 1 (2015), pp. 510-515
- ²⁹ K. B. Knudsen, A. Luntz, S. Jensen, T. Vegge, J. Hjelm, **A Redox Probing Study of the Potential Dependence of Charge Transport through Li₂O₂**, *J. Phys. Chem. C*, 119 (2015), pp. 28292-28299
- ³⁰ B. D. McCloskey and D. Addison, **A Viewpoint on Heterogeneous Electrocatalysis and Redox Mediation in Nonaqueous Li-O₂ Batteries**, *ACS Catalysis*, 7 (2017), pp. 772-778
- ³¹ X. Gao, Y. Chen, L. Johnson and P. G. Bruce, **Promoting solution phase discharge in Li-O₂ batteries containing weakly solvating electrolyte solutions**, *Nature Mater.*, 15 (2016), pp. 882-888
- ** Demonstrates how the use of a homogeneous catalyst for O₂ reduction can result in a new solution based mechanism, which may improve capacity and cycle life.
- ³² X. Yao, Q. Dong, Q. Cheng and D. Wang, **Why Do Lithium-Oxygen Batteries Fail: Parasitic Chemical Reactions and Their Synergistic Effect**, *Angew. Chem. Int. Ed.*, 55 (2016), pp. 11344-11353
- ³³ R. Younesi, G. M. Veith, P. Johansson, K. Edström, T. Vegge, **Lithium Salts for Advanced Lithium Batteries: Li-metal, Li-O₂, and Li-S**, *Energy & Environ. Sci.*, 8 (2015), pp. 1905-1922
- ³⁴ B. D. McCloskey, A. Valery, A. C. Luntz, S. R. Gowda, G. M. Wallraff, J. M. Garcia, T. Mori and L. E. Krupp, **Combining Accurate O₂ and Li₂O₂ Assays to Separate Discharge and Charge Stability Limitations in Nonaqueous Li-O₂ Batteries**, *J. Phys. Chem. Lett.*, 4 (2012), pp. 2989-2993
- ³⁵ A. C. Luntz and B. D. McCloskey, **Importance of singlet oxygen**, *Nature Energy*, 2 (2017), 17056
-

* Outlines the implications of singlet oxygen on the electrolyte and electrode degradation.

³⁶ J. Wandt, P. Jakes, J. Granwehr, H. A. Gasteiger, and R.-A. Eichel, **Singlet Oxygen Formation during the Charging Process of an Aprotic Lithium–Oxygen Battery**, *Angew. Chem. Int. Ed.*, 128 (2016), pp. 7006-7009

** Provides the first evidence for the formation of reactive singlet oxygen during charge.

³⁷ N. Mahne, B. Schafzahl, C. Leypold, M. Leypold, S. Grumm, A. Leitgeb, G. A. Strohmeier, M. Wilkening, O. Fontaine, D. Kramer, C. Slugovc, S. M. Borisov and S. A. Freunberger, **Singlet oxygen generation as a major cause for parasitic reactions during cycling of aprotic lithium–oxygen batteries**, *Nature Energy*, 2 (2017), 17036

** Shows that singlet oxygen is formed already at the onset of charge and via disproportionation of LiO₂.

³⁸ J. Yi, S. Guo, P. He and H. Zhou, **Status and prospects of polymer electrolytes for solid-state Li–O₂ (air) batteries**, *Energy & Environ. Sci.*, 10 (2017), pp. 860-884

³⁹ C. V. Amanchukwu, H.-H. Chang, M. Gauthier, S. Feng, T. P. Batcho and P. T. Hammond, **One-Electron Mechanism in a Gel–Polymer Electrolyte Li–O₂ Battery**, *Chem. Mater.* 28 (2016), pp. 7167–7177

⁴⁰ P. He, T. Zhang, J. Jiang, and H. Zhou, **Lithium–Air Batteries with Hybrid Electrolytes**, *J. Phys. Chem. Lett.*, 7 (2016), pp. 1267-1280

⁴¹ Y. Li, X. Wang, S. Dong, X. Chen and G. Cui, **Recent Advances in Non-Aqueous Electrolyte for Rechargeable Li–O₂ Batteries**, *Adv. Energy Mater.* 6 (2016), 1600751

⁴² C. J. Allen, S. Mukerjee, E. J. Plichta, M. A. Hendrickson, K. Abraham, **Oxygen Electrode Rechargeability in an Ionic Liquid for the Li–Air Battery**, *J. Phys. Chem. Lett.*, 2 (2011), 2420

⁴³ G. A. Elia, J. Hassoun, W.-J. Kwak, Y.-K. Sun, B. Scrosati, F. Mueller, D. Bresser, S. Passerini, P. Oberhumer, N. Tsiouvaras, **An Advanced Lithium–Air Battery Exploiting an Ionic Liquid-Based Electrolyte**, *Nano Lett.*, 14 (2014), 6572

⁴⁴ B. D. McCloskey, D. S. Bethune, R. M. Shelby, T. Mori, R. Scheffler, A. Speidel, M. Sherwood, A. C. Luntz, **Limitations in Rechargeability of Li–O₂ Batteries and Possible Origins**, *J. Phys. Chem. Lett.*, 3 (2012), pp. 3043–3047

⁴⁵ S. Das, J. Højberg, K. B. Knudsen, R. Younesi, P. Johansson, P. Norby and T. Vegge, **Instability of Ionic Liquid Based Electrolytes in Li–O₂ Batteries**, *J. Phys. Chem. C*, 119 (2015), pp. 18084-18090

⁴⁶ V. Giordani, D. Tozier, H. Tan, C. M. Burke, B. M. Gallant, J. Uddin, J. R. Greer, B. D. McCloskey, G. V. Chase and D. Addison, **A Molten Salt Lithium–Oxygen Battery**, *J. Am. Chem. Soc.*, 138 (2016), pp. 2656–2663

** Demonstrates the high potential for use of stable molten-salt electrolytes in Li–O₂ batteries.

⁴⁷ P. He, T. Zhang, J. Jiang and H. Zhou, **Lithium–Air Batteries with Hybrid Electrolytes**, *J. Phys. Chem. Lett.*, 7 (2016), 1267-1280

⁴⁸ L. Luo, B. Liu, S. Song, W. Xu, J.-G. Zhang and C. Wang, **Revealing the reaction mechanisms of Li–O₂ batteries using environmental transmission electron microscopy**, *Nature Nanotechnology*, 12 (2017), pp. 535–539

** Uses *in situ* TEM to reveal the Li–O₂ reaction mechanism in a solid electrolyte (in real time).

⁴⁹ Y. Li, X. Wang, S. Dong, X. Chen and G. Cui, **Recent Advances in Non-Aqueous Electrolyte for Rechargeable Li–O₂ Batteries**, *Adv. Energy Mater.*, 6 (2016), 1600751

⁵⁰ * K. Fu, Y. Gong, L. Boyang, Y. Zhu, S. Xu, Y. Yao, W. Luo, C. Wang, S. D. Lacey, J. Dai, Y. Chen, Y. Mo, E. Wachsman, L. Hu, **Toward garnet electrolyte–based Li metal batteries: An ultrathin, highly effective, artificial solid-state electrolyte/metallic Li interface**, *Sci. Adv.*, 3 (2017), e1601659

-
- ⁵¹ A. Sharafi, S. Yu, M. Naguib, M. Lee, C. Ma, H. M. Meyer, J. Nanda, M. Chi, D. J. Siegel, and J. Sakamoto, **Impact of Air Exposure and Surface Chemistry on Li-Li₇La₃Zr₂O₁₂ Interfacial Resistance**, *J. Mater. Chem. A*, 5 (2017), pp. 13475-13487
- ⁵² T. Thompson, S. Yu, L. Williams, R. D. Schmidt, R. Garcia-Mendez, J. Wolfenstine, J. L. Allen, E. Kioupakis, D. J. Siegel, and J. Sakamoto, **Electrochemical Window of the Li-ion Solid Electrolyte Li₇La₃Zr₂O₁₂**, *ACS Energy Lett.*, 2 (2017), pp. 462-468
- ⁵³ S. Yu, R. D. Schmidt, R. Garcia-Mendez, E. Herbert, N. J. Dudney, J. B. Wolfenstine, J. Sakamoto, and D. J. Siegel, **Elastic Properties of the Solid Electrolyte Li₇La₃Zr₂O₁₂ (LLZO)**, *Chem. Mater.*, 28 (2015), pp. 197-206
- ⁵⁴ D. Blanchard, A. Nale, D. Sveinbjörnsson, T.M. Eggenhuisen, M.H.W. Verkuijlen, Suwarno, T. Vegge, A. P. M. Kentgens, and P. E. de Jongh, **Nanoconfined LiBH₄ as a fast lithium ion conductor**, *Adv. Func. Mater.*, 25 (2015), pp. 184-192
- ⁵⁵ P. Hartmann, C. L. Bender, M. Vračar, A. K. Dürr, A. Garsuch, J. Janek and P. Adelhelm, **A rechargeable room-temperature sodium superoxide (NaO₂) battery**, *Nature Mater.*, 12 (2013), pp. 228-232
- ⁵⁶ K. B. Knudsen, J. E. Nichols, T. Vegge, A. C. Luntz, B. D. McCloskey, J. Hjelm, **An Electrochemical Impedance Study of the Capacity Limitations in Na-O₂ Cells**, *J. Phys. Chem. C*, 120 (2016), pp. 10799-10805
- ⁵⁷ J. Lu, Y. J. Lee, X. Luo, K. C. Lau, M. Asadi, H.-H. Wang, S. Brombosz, J. Wen, D. Zhai, Z. Chen, D. J. Miller, Y. S. Jeong, J.-B. Park, Z. Z. Fang, B. Kumar, A. Salehi-Khojin, Y.-K. Sun, L. A. Curtiss and K. Amine, **A lithium-oxygen battery based on lithium superoxide**, *Nature*, 529 (2016), pp. 377-383
- ** Reports that formation of a solid LiO₂ discharge product can be promoted by use of Ir-nanoparticles on reduced Graphene oxide (rGO).
- ⁵⁸ K. C. Lau, L. A. Curtiss, J. Greeley, **Density Functional Investigation of the Thermodynamic Stability of Lithium Oxide Bulk Crystalline Structures as a Function of Oxygen Pressure**, *J. Phys. Chem. C*, 115 (2011), pp. 23625-23633
- ⁵⁹ S. Li, J. Liu and B. Liu, **First-Principles Study of the Charge Transport Mechanisms in Lithium Superoxide**, *Chem. Mater.*, 29 (2017), pp. 2202-2210
- ⁶⁰ B. Lee, J. Kim, G. Yoon, H.-D. Lim, I.-S. Choi, K. Kang, **Theoretical Evidence for Low Charging Overpotentials of Superoxide Discharge Products in Metal-Oxygen Batteries**, *Chem. Mater.*, 27 (2015), pp. 8406-8413
- ⁶¹ S. Yang and D. J. Siegel, **Intrinsic Conductivity in Sodium-air Battery Discharge Phases: Sodium Superoxide vs. Sodium Peroxide**, *Chem. Mater.*, 27 (2015), 3852
- ⁶² O. Gerbig, R. Merkle, and J. Maier, **Electrical Transport and Oxygen Exchange in the Superoxides of Potassium, Rubidium, and Cesium**, *Adv. Func. Mater.*, 25 (2015), pp. 2552-2563
- ⁶³ C. C. Fischer, **A Machine Learning Approach to Crystal Structure Prediction**, Ph.D., Massachusetts Institute of Technology, 2007.
- ⁶⁴ H. S. C. O'Neill and J. Nell, **Gibbs free energies of formation of RuO₂, IrO₂, and OsO₂: A high-temperature electrochemical and calorimetric study**, *Geochimica et Cosmochimica Acta*, 61 (1997), pp. 5279-5293
- ⁶⁵ V. Pfeifer, T. E. Jones, J. J. Velasco Vélez, C. Massué, R. Arrigo, D. Teschner, F. Girgsdies, M. Scherzer, M. T. Greiner, J. Allan et al., **The electronic structure of iridium and its oxides**, *Surface Interf. Anal.*, 48 (2016), pp. 261-273
- ⁶⁶ E. McCalla, A. M. Abakumov, M. Saubanère, D. Foix, E. J. Berg, G. Rousse, M.-L. Doublet, D. Gonbeau, P. Novák, G. V. Tendeloo, R. Dominko, J.-M. Tarascon, **Visualization of O-O peroxo-like dimers in high-capacity layered oxides for Li-ion batteries**, *Science*, 350 (2015), pp. 1516 -1521
-

⁶⁷ P. E. Pearce, A. J. Perez, G. Rousse, M. Saubanere, D. Batuk, D. Foix, E. McCalla, A. M. Abakumov, G. Van Tendeloo, M.-L. Doublet et al., **Evidence for anionic redox activity in a tridimensional-ordered Li-rich positive electrode b-Li₂IrO₃**. *Nature Mater.*, 16 (2017), pp. 580-586

⁶⁸ M. J. O'Malley, H. Verweij and P. M. Woodward, **Structure and properties of ordered Li₂IrO₃ and Li₂PtO₃**, *J. Solid State Chem.*, 181 (2008), pp. 1803-1809

⁶⁹ H. Kobayashi, M. Tabuchi, M. Shikano, H. Kageyama and R. Kanno, **Structure, and magnetic and electrochemical properties of layered oxides, Li₂IrO₃**, *J. Mater. Chem.*, 13 (2003), pp. 957-962

⁷⁰ Y. Shen, W. Zhang, S.-L. Chou, S.-X. Dou, **Comment on "Cycling Li-O₂ batteries via LiOH formation and decomposition"**, *Science*, 352 (2016), 667-a

* Proposes an alternative reaction mechanism to account for the observations made by Liu *et al.* in Ref. [6].

⁷¹ V. Viswanathan, V. Pande, K. M. Abraham, A. C. Luntz, B. D. McCloskey, D. Addison, **Comment on "Cycling Li-O₂ batteries via LiOH formation and decomposition"**, *Science*, 352 (2016), 667-c

* Argues that limited-capacity cycling can conceal important parasitic side reactions.

⁷² T. Liu, G. Kim, J. Carretero-González, E. Castillo-Martínez, C. P. Grey, **Response to Comment on "Cycling Li-O₂ batteries via LiOH formation and decomposition"**, *Science*, 352 (2016), 667-b

⁷³ T. Liu, G. Kim, J. Carretero-González, E. Castillo-Martínez, C. P. Grey, **Response to Comment on "Cycling Li-O₂ batteries via LiOH formation and decomposition"**, *Science*, 352 (2016), 667-d

⁷⁴ C. M. Burke, R. Black, I. R. Kochetkov, V. Giordani, D. Addison, L. F. Nazar and B. D. McCloskey, **Implications of 4 e⁻ Oxygen Reduction via Iodide Redox Mediation in Li-O₂ Batteries**, *ACS Energy Lett.*, 1 (2016), pp. 747-756

* Shows that the presence of LiI and H₂O can promote a 4-electron oxygen reduction to LiOH, but the LiOH is not reversibly oxidized to O₂ on charge.
