



## X-ray tomography data of White Etching Cracks (WEC)

**Fæster, Søren; Danielsen, Hilmar Kjartansson**

*Published in:*  
Data in Brief

*Link to article, DOI:*  
[10.1016/j.dib.2019.104531](https://doi.org/10.1016/j.dib.2019.104531)

*Publication date:*  
2019

*Document Version*  
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

*Citation (APA):*  
Fæster, S., & Danielsen, H. K. (2019). X-ray tomography data of White Etching Cracks (WEC). *Data in Brief*, 27, [104531]. <https://doi.org/10.1016/j.dib.2019.104531>

---

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.



ELSEVIER

Contents lists available at ScienceDirect

## Data in brief

journal homepage: [www.elsevier.com/locate/dib](http://www.elsevier.com/locate/dib)

Data Article

## X-ray tomography data of White Etching Cracks (WEC)



Søren Fæster\*, Hilmar K. Danielsen

*Department of Wind Energy, Technical University of Denmark, Risø Campus, Frederiksborgvej 399, 4000, Roskilde, Denmark*

## ARTICLE INFO

*Article history:*

Received 1 July 2019

Received in revised form 26 August 2019

Accepted 9 September 2019

Available online 17 September 2019

*Keywords:*

White Etching Crack

X-ray tomography

Bearing

Wind turbine

## ABSTRACT

This data article contains lab-based micro-computed tomography ( $\mu$ CT) data of cracks and crack networks in 4 different bearings, mainly from wind turbines, which formed the basis for the crack analysis reported in Danielsen et al. (Danielsen et al., 2019).

© 2019 Published by Elsevier Inc. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

**1. Data**

The data presented in this paper consist of 5 X-ray tomography datasets of crack networks found in 4 different types of bearings. Sample A is an axial bearing from an FE8 type test rig and two volumes have been scanned on this sample. These scans are labelled Sample A1 and Sample A2 (Fig. 1 and Fig. 2). Sample B is a tapered bearing (Fig. 3), Sample C is a ball bearing (Fig. 4) and Sample D is a radial bearing (Fig. 5). Samples B, C and D are all from wind turbine bearings. The original raceway is marked with an arrow while the running direction is unknown. The scan parameters for all the scans are listed in Table 1 and the datasets are all in 3D tif format.

\* Corresponding author.


E-mail address: [sfni@dtu.dk](mailto:sfni@dtu.dk) (S. Fæster).

## Specifications Table


|                                |  |
|--------------------------------|--|
| Subject                        | Metals and Alloys  |
| Specific subject area          | X-ray tomography of White etching cracks (WEC) in wind turbine bearing   |
| Type of data                   | X-ray tomography data  |
| How data were acquired         | Laboratory X-ray tomography scanner (Zeiss Xradia 520 Versa)   |
| Data format                    | 3D tif images  |
| Parameters for data collection | The bearings were cut into size before scanning with the experimental settings listed in Table 1   |
| Description of data collection | Absorption X-ray tomography and reconstruction by standard filtered back projecting  |
| Data source location           | Roskilde, Denmark, Latitude: 55.695343, Longitude: 12.08921  |
| Data accessibility             | The data is available online at: <a href="https://doi.org/10.5281/zenodo.3237622">https://doi.org/10.5281/zenodo.3237622</a> <a href="https://doi.org/10.5281/zenodo.3258273">https://doi.org/10.5281/zenodo.3258273</a> <a href="https://doi.org/10.5281/zenodo.3258682">https://doi.org/10.5281/zenodo.3258682</a> <a href="https://doi.org/10.5281/zenodo.3259000">https://doi.org/10.5281/zenodo.3259000</a>   |
| Related research article       | The datasets presented in this paper have been used in [1] to determine cracks and crack networks in 4 different types of wind turbine bearings.<br>[1] H.K. Danielsen, S. Fæster, A.J. Carrasco, K.V. Dahl, F.G. Guzmán, P. Sauvage, G. Jacobs, 3D X-ray Computerized Tomography of White Etching Cracks (WEC), Materials Characterization 150 (2019) 78–87.<br><a href="https://doi.org/10.1016/j.matchar.2019.01.032">https://doi.org/10.1016/j.matchar.2019.01.032</a> |

## Value of the Data


- The datasets contain detailed 3D information of crack formation in different types of wind turbine bearings, showing different crack morphology types in three dimensions.
- The datasets makes it possible to observe damage progression inside the specimens in 3D, which could enhance the understanding of the damage mechanisms and initiation.
- The datasets can serve as input for 3D fracture mechanics models dealing with the damage progression of cracks in bearings.
- The datasets can be used for developing better segmentation algorithm for determination of crack networks.

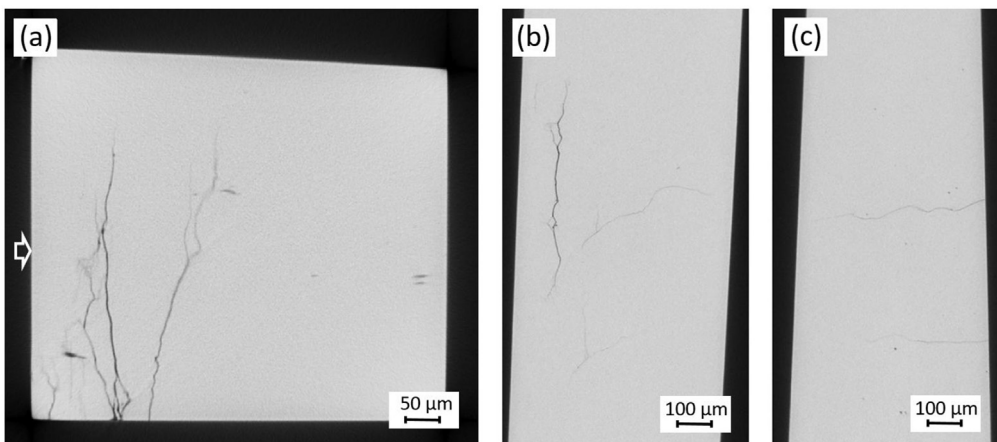


**Fig. 1.** Sample A1. Cross sections through the middle of the dataset in the directions (a) xy, (b) xz and (c) yz. The white arrow in (a) indicate the original raceway.

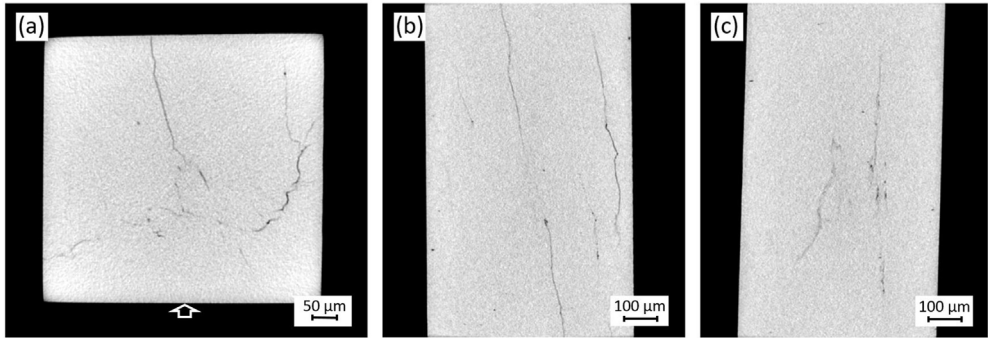


**Fig. 2.** Sample A2. Cross sections through the middle of the dataset in the directions (a) xy, (b) xz and (c) yz. The white arrow in (a) indicate the original raceway.

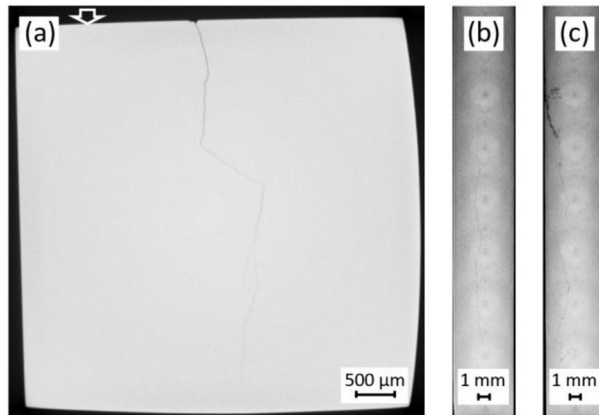

**Fig. 3.** Sample B. Cross sections through the middle of the dataset in the directions (a) xy, (b) xz and (c) yz. The white arrow in (a) indicate the original raceway.

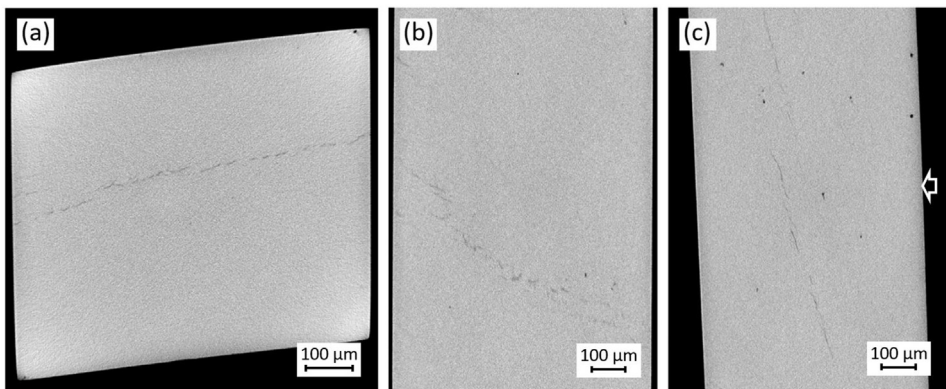

**Fig. 4.** Sample C. Cross sections through the middle of the dataset in the directions (a) xy, (b) xz and (c) yz. The white arrow in (c) indicate the original raceway.

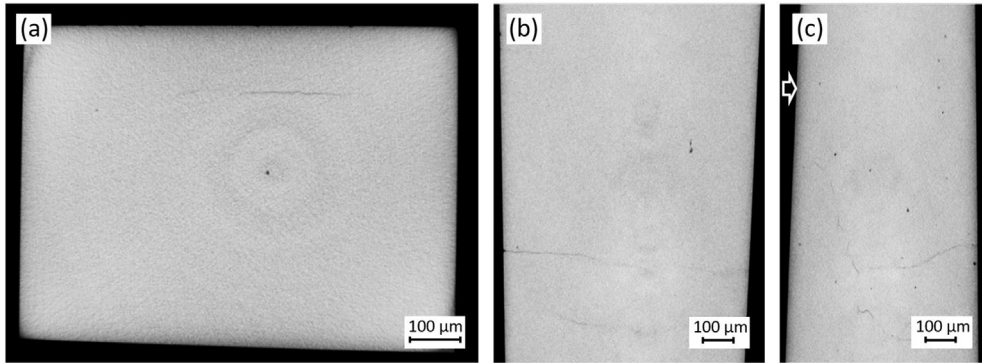

**Fig. 5.** Sample D. Cross sections through the middle of the dataset in the directions (a) xy, (b) xz and (c) yz. The white arrow in (c) indicate the original raceway.

**Table 1**

X-ray tomography settings.

| Parameter                        | Sample A1     | Sample A2     | Sample B        | Sample C     | Sample D       |
|----------------------------------|---------------|---------------|-----------------|--------------|----------------|
|                                  | Axial Bearing | Axial bearing | Tapered bearing | Ball Bearing | Radial bearing |
| Optical magnification            | 4X            | 4X            | 4X              | 4X           | 4X             |
| Source to sample distance (mm)   | 8.18          | 11.02         | 15.10           | 8.10         | 7.87           |
| Detector to sample distance (mm) | 31.15         | 65.00         | 115.04          | 37.27        | 33.00          |
| Exposure time (sec)              | 10            | 10            | 10              | 15           | 20             |
| No. of projections               | 4001          | 1601          | 3001            | 3201         | 3201           |
| Rotation                         | 360°          | 360           | 360°            | 360°         | 360°           |
| Accelerating voltage (kV)        | 80            | 90            | 160             | 80           | 90             |
| Binning                          | 1             | 1             | 1               | 1            | 1              |
| Pixel size (μm)                  | 0.70          | 0.49          | 3.96            | 0.60         | 0.65           |
| Source filter                    | LE6           | HE1           | HE5             | LE6          | HE2            |
| Stitching                        | 1             | 1             | 8               | 1            | 1              |
| Reconstruction filter (smooth)   | 0.7           | 2.5           | 1.0             | 0.7          | 1.6            |
| Beam hardening correction        | 0.16          | 0.16          | 0.11            | 0.13         | 0.16           |

## 2. Experimental design, materials, and methods

The specimens that have been scanned consist of four different types of bearings, mainly from wind turbines, that are all containing cracks. The reader is referred to [1] for a detailed description of how the samples were manufactured. The tomography scans were performed on a Zeiss Xradia 520 Versa. The X-ray scanner was equipped with a tungsten target. An acceleration voltage of 30 kV and a power of 10 mA was applied to generate X-rays with energies up to 160 keV. Projections were acquired during a full 360° rotation of the specimens.

The detector size was  $2k \times 2k$  and projection images with a binning of 1 were acquired to obtain highest possible resolution. A Feldkamp reconstruction algorithm [2] for cone beam reconstructions was applied resulting in 3D reconstructions with voxel sizes down to 0.49 μm. All relevant scan parameters are listed in Table 1.

## Acknowledgments

The data was acquired using the Zeiss Xradia 520 Versa from the DTU Centre for Advanced Structural and Material Testing (CAS-MAT), grant no. VKR023193 from Villum Fonden.

### **Conflict of interest**

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

### **References**

- [1] H.K. Danielsen, S. Fæster, A.J. Carrasco, K.V. Dahl, F.G. Guzmán, P. Sauvage, G. Jacobs, 3D X-ray computerized tomography of white etching cracks (WEC), *Mater. Char.* 150 (2019) 78–87.
- [2] L.A. Feldkamp, L.C. Davis, J.W. Kress, Practical cone-beam algorithm, *J. Opt. Soc. Am. A* 1 (6) (1984) 612–619.