



Methanol-assisted autocatalysis in catalytic methanol synthesis

Thrane, Joachim; Kuld, Sebastian; Nielsen, Niels D.; Jensen, Anker D.; Sehested, Jens; Christensen, Jakob M.

Published in:
Angewandte Chemie International Edition

Link to article, DOI:
[10.1002/anie.202006921](https://doi.org/10.1002/anie.202006921)

Publication date:
2020

Document Version
Peer reviewed version

[Link back to DTU Orbit](#)

Citation (APA):
Thrane, J., Kuld, S., Nielsen, N. D., Jensen, A. D., Sehested, J., & Christensen, J. M. (2020). Methanol-assisted autocatalysis in catalytic methanol synthesis. *Angewandte Chemie International Edition*, 59(41), 18189-18193. <https://doi.org/10.1002/anie.202006921>

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Methanol assisted autocatalysis in catalytic methanol synthesis

Joachim Thrane^[a], Sebastian Kuld^[b], Niels D. Nielsen^[a], Anker D. Jensen^[a], Jens Sehested^[b] and Jakob M. Christensen*^[a]

^[a] Department of Chemical and Biochemical Engineering

Technical University of Denmark

Søltofts Plads B229, 2800 Kgs. Lyngby (Denmark)

^[b] Haldor Topsøe A/S

Nymøllevej 55, 2800 Kgs. Lyngby (Denmark)

Abstract: Catalytic methanol synthesis is one of the major processes in the chemical industry and may grow in importance, as methanol produced from CO₂ and sustainably derived H₂ is envisioned to play an important role as energy carrier in a future low CO₂ emission society. However, despite the widespread use, the reaction mechanism and the nature of the active sites are not fully understood. Here we report that methanol synthesis at commercially applied conditions using the industrial Cu/ZnO/Al₂O₃ catalyst is dominated by a methanol-assisted, autocatalytic reaction mechanism. We propose that the presence of methanol opens for hydrogenation of surface formate via methyl formate. Autocatalytic acceleration of the reaction is also observed for Cu supported on SiO₂ although with low absolute activity, but not for Cu/Al₂O₃ catalysts. The results illustrate an important example of autocatalysis in heterogeneous catalysis and pave the way for further understanding, improvements and process optimization of industrial methanol synthesis.

Introduction

Heterogeneous catalysis is vital to modern chemical industry. Understanding the nature of the active sites, reaction mechanisms and the origin of metal-support/promoter interactions is therefore not only fundamentally important, but also significant due to the substantial economic impact of improvements to large-scale industrial processes relying on catalysis. Methanol is a major bulk chemical with a production exceeding 70 million tons/year and is produced from syngas (CO/CO₂/H₂) over a Cu/ZnO/Al₂O₃ catalyst^[1]. Methanol synthesis can proceed over Cu surfaces, but the reaction rate is strongly enhanced by the presence of zinc in the catalyst^[2-5]. However, the exact nature of the active sites and the beneficial support effect from ZnO in the industrial catalyst are still debated issues. By contrast, there seems to be a more widespread agreement concerning the general reaction mechanism for methanol synthesis over Cu catalysts. Most theoretical and experimental studies advocate that methanol is made directly from carbon dioxide (CO₂) and hydrogen (H₂) via formation of surface formate and its subsequent hydrogenation to methanol, and this reaction mechanism explains most reported data in the literature. Yet, such a mechanism is not able to explain some of the most remarkable observations, where methanol synthesis rates under certain conditions are accelerated with increasing conversion^[6, 7]. This acceleration is highly unexpected, as the methanol synthesis has a relatively unfavourable equilibrium and experiences a strong kinetic inhibition from the accompanying water product^[7-10]. Here, we demonstrate that the origin of this obvious inconsistency between theoretical understanding and experimental data is a previously unknown, methanol-assisted, autocatalytic reaction pathway. Our data confirm that this reaction pathway is responsible for most of the turnovers to methanol under industrial conditions, and we conclude that the autocatalytic mechanism most likely is via a methyl formate intermediate.

Results and Discussion

A series of Cu catalysts supported on ZnO/Al₂O₃, ZnO, Al₂O₃ and SiO₂ were prepared, and the active Cu areas of the catalysts were determined through the oxygen uptake (using O:Cu_{surf.} 1:2 and $1.47 \cdot 10^{19}$ Cu atoms/m²)^[11] from 1 mol% N₂O/He at 333 K after reduction in 5 vol% H₂/N₂ at atmospheric pressure and 523 K. Cu/Al₂O₃ required that the 5% H₂/N₂ treatment was followed by a 100% H₂ treatment at 523 K to obtain complete Cu reduction. The catalytic activity of pre-reduced catalysts was measured in a flow reactor at 523 K and 50 bar in syngas (CO/CO₂/H₂ = 29.6/2.8/67.6 mol%), and for each catalyst, the space velocity (SV) was varied by 1-3 orders of magnitude to vary the level of conversion. Turnover frequencies (TOF: methanol formation rate per Cu surface atom) at the different conversion levels were determined from the Cu surface areas and the methanol production rates, and Fig. 1 shows the TOF as a function of the methanol concentration at the exit of the reactor.


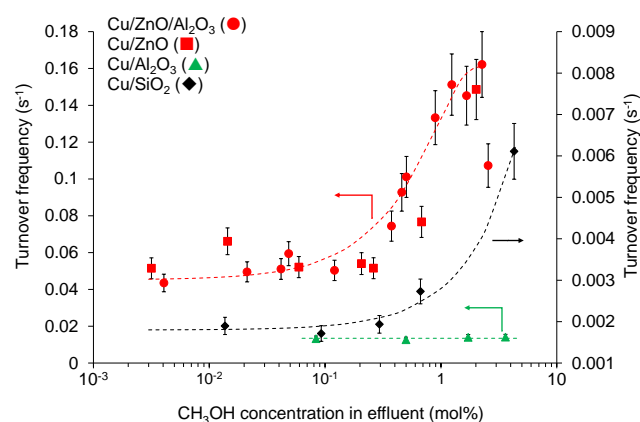


Fig. 1. The dependence of the TOF upon the CH₃OH concentration in the reactor effluent when varying the space velocity. Note the different scaling of the Cu/SiO₂ data. Dashed lines given as guides to the eye. Experimental conditions: 50 bar, 523 K, H₂/CO/CO₂ = 67.6/29.6/2.8 mol%, $3 \cdot 10^3$ - $4.3 \cdot 10^7$ NL/kg/h. See Fig. S1 for a definition of the TOF and a comparison in terms of space velocity. The equilibrium concentration of CH₃OH at these conditions is 23 mol% based on data from Graaf and Winkelman^[12].

This figure depicts, how the Cu catalysts respond to the changing product concentrations, when the SV is varied. Under differential conditions (below approximately 0.1 mol% methanol produced), the TOF reaches a stable plateau for each catalyst type. Here methanol formation through a mechanism directly from the reactants must dominate. At these conditions there is a notable support effect on the TOF, and the activity order of the supports (ZnO/Al₂O₃ \cong ZnO > Al₂O₃ > SiO₂) is in good agreement with the observations in several previous studies^[2-4]. Within the uncertainty the same TOF is seen for Cu/ZnO/Al₂O₃ and Cu/ZnO at identical conversion levels in Fig. 1, and these two systems are therefore treated collectively in the remaining text. The TOF-values are determined from the Cu surface areas obtained from N₂O titrations, and there are uncertainties in methods for determination of metal area, as illustrated by the systematic and carrier-dependent differences between areas from N₂O and H₂ titrations^[11]. However, with the applied pre-reduction, the magnitude of these differences^[11] is expected to be considerably smaller than the differences between the TOF values of the different catalyst systems, and the uncertainties on the area should therefore not affect the conclusions. Consequently, this issue is not discussed further in the following.

Remarkable changes in TOF are observed in Fig. 1 when the product concentrations are increased by lowering of the SV to achieve finite conversions. Lowering the SV causes the TOF-

values for the ZnO(/Al₂O₃) and SiO₂ containing catalysts to increase more than three-fold. Such an increase with rising product concentration is indicative of a significant autocatalytic effect, whereby the product assists the formation of additional product. The magnitude of the acceleration means that the autocatalytic pathway is at least several times faster than the direct pathway, and as a result the substantial majority of turnovers in the industrial process must arise from the autocatalytic pathway. This autocatalytic behaviour is clearly support-dependent. The Cu/SiO₂ catalyst has a low absolute activity but shows an autocatalytic behaviour like that of Cu/ZnO(/Al₂O₃), while reaction rates for Cu/Al₂O₃ are independent of SV (see also Supporting Information Fig. S1d). The heat generated in the exothermic reaction increases with conversion/product concentration regardless of the support, but here no significant temperature rise was observed, and the fact that TOF for Cu/Al₂O₃ did not grow with conversion shows that the acceleration is not due to a temperature rise. As CO₂ is the primary reactant in methanol synthesis over pure Cu and Cu/ZnO(/Al₂O₃)^[9, 13, 14] it is important to evaluate, if changes in CO₂ concentration can arise from the variations in conversion. CO₂ is consumed via methanol synthesis (R1), but partly restored by the water-gas shift reaction (R2).



The activity peak for Cu/ZnO(/Al₂O₃) in Fig. 1 (+372%) occurs at 2 mol% methanol in the effluent. If R2 is equilibrated at these conditions there will be a 2.5% net conversion of the CO₂. However, the volume contraction due to the loss of molecules in R1 was measured to be 4% at these conditions, and this leads to a corresponding rise in the CO₂ concentration. The consumption of CO₂ and the concentration rise due to volume contraction thus nearly balance out, and the concentration of CO₂ is therefore essentially unaffected by the reaction (see Fig. S2). Consequently, reaction-induced changes in CO₂ concentration cannot affect the experimental results. As diffusion limitations were ruled out by experiments and calculations (see Supporting Information), it can be ruled out that a local concentration rise within the catalyst pores should affect this conclusion.

The increase in reaction rate in Fig. 1 must therefore arise from the emergence of a faster pathway at higher conversions, and at least two parallel reaction pathways in methanol synthesis are needed to explain the results: a direct conversion of the reactants dominating at differential conditions and a faster autocatalytic route involving a reaction product dominant at higher conversions. At the lower SV, where the autocatalytic pathway prevails, the TOF for Cu/ZnO was observed to remain constant across an 8-fold variation in Cu surface area, which corresponds to a linear correlation between absolute activity and Cu surface area (Fig. S3). This would imply that the rate limiting step in the autocatalytic pathway occurs on the metal surface, but there is clearly also an either direct or indirect involvement of the support that is of great importance for the absolute activity.

In the industrial process the syngas feed already contains some methanol due to recirculation of unconverted reactants, and the methanol concentration rises to significant percentages through the reactor^[15]. Under such conditions, the faster autocatalytic pathway will be responsible for the vast majority of the turnovers and thus dominate the industrial process.

This conclusion raises the question of, which reaction product that causes such an effect. As the highly selective methanol synthesis produces only two major products, namely CH₃OH and H₂O, these two products represent the most likely candidates. Additional experiments were therefore conducted with the Cu/ZnO/Al₂O₃ catalyst (Cu:Zn:Al = 6:3:1, 20 m_{Cu}²/g_{cat.}) to identify the source and possible mechanism of the autocatalytic effect. The methanol synthesis activity was measured for the Cu/ZnO/Al₂O₃ catalyst at differential conditions (SV = 1.6 · 10⁶ NL/kg/h) far from equilibrium (< 1000 ppm CH₃OH produced) with low levels of water added to the syngas feed, and the results are shown in Fig. 2.

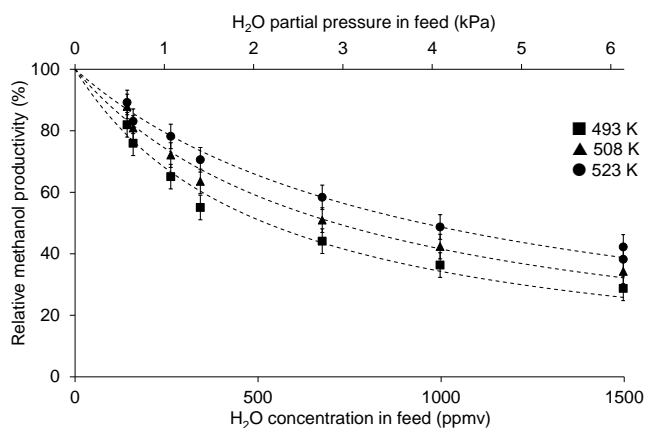


Fig. 2. The relative methanol production as a function of the water content added to the syngas feed. Experimental conditions: Catalyst: Cu/ZnO/Al₂O₃, P = 41 bar, H₂/CO/CO₂ = 67.6/29.6/2.8 mol%, 1.6 · 10⁶ NL/kg/h. Dashed lines given as guides to the eye. See Supporting Information for a definition of the error bars.

The data in Fig. 2 illustrate that even minute amounts of water lower the activity substantially, which strongly indicates that water is not the source of the autocatalytic effect. Competitive adsorption of water or its dissociation products is a likely explanation for this kinetic inhibition, as water adsorption isotherm measurements^[16, 17] on Cu/ZnO/Al₂O₃ suggest a high coverage on the Cu surface at temperatures and H₂O partial pressures similar to those where major water inhibition is observed in Fig. 2. The increase in TOF with rising product concentrations in Fig. 1 is even more remarkable when considering the strong inhibition caused by the co-produced water.

The effect of adding the second major product, methanol, to the syngas feed is illustrated in Fig. 3. Two independent methanol co-feeding experiments were performed in two very different setups (described in detail in the Supporting Information), and the results are depicted as Figs. 3a and 3b, respectively. Remarkably, the net rate of methanol formation increases considerably, when methanol is co-fed with the syngas feed, and on this basis we deduce that methanol is the source of the autocatalytic acceleration in methanol synthesis.

Liquid phase alcohols were previously found^[18-20] to accelerate the Cu-catalysed hydrogenation of CO₂ to methanol at low temperatures ($\leq 443\text{K}$) well below the industrial operating window. However, the data in Fig. 3 imply that methanol synthesis at commercial conditions is dominated by methanol mediated autocatalysis.


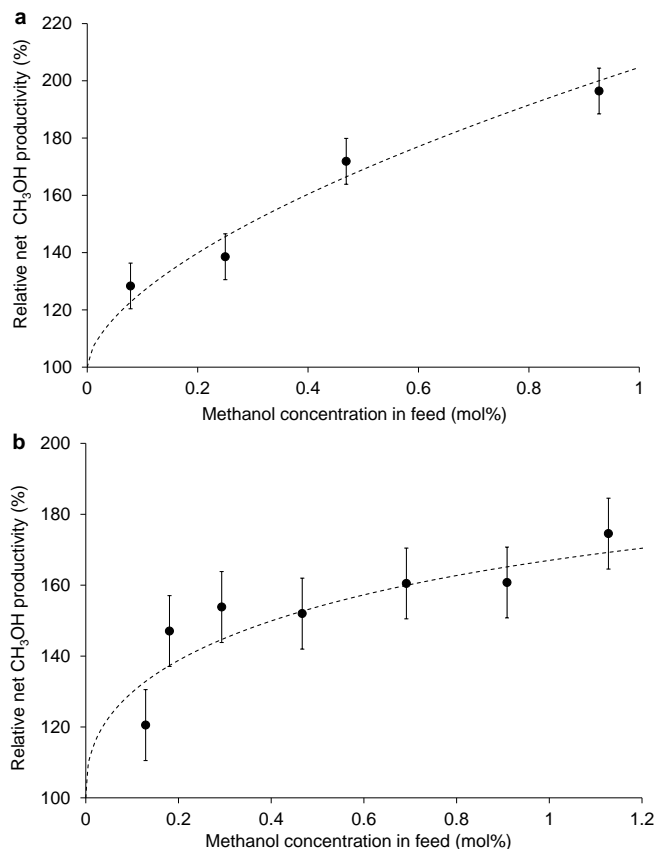


Fig. 3. (a) Relative net productivity of methanol as a function of the methanol concentration in the syngas feed at 50 bar. (b) Relative net productivity of methanol as a function of the methanol concentration in the syngas feed at 41 bar. Other experimental conditions: Catalyst: Cu/ZnO/Al₂O₃, T = 523 K, syngas before MeOH addition: H₂/CO/CO₂ = 67.6/29.6/2.8 mol%, $1.6 \cdot 10^6$ NL/kg/h. Additional data in Figs. S4 and S5. See Supporting Information for a definition of the error bars.

The net increase in reaction rate with increasing conversion seen in a CO/CO₂/H₂ feed (Fig. 1) does not occur in CO₂/H₂ gas mixtures as illustrated in Fig. S6. This can be rationalized through the opposite effects of the two reaction products. If CO is present, most of the produced water will be removed by R2, and the beneficial effect of methanol will dominate over the adverse effect of water. In a CO-free atmosphere, water is produced by both the methanol synthesis and the reverse water-gas shift reaction, and the greater concentration of inhibiting water causes the rate to decline with increasing conversion. However, from a CO₂/H₂ feed, only a moderate loss in activity of 6% was observed for a Cu/ZnO/Al₂O₃ catalyst at a methanol effluent concentration of 0.4 mol% (see Fig. S6). At these conditions, an oxygen balance suggested that 0.68 mol% water was co-produced, if only R1 and R2 occur. Considering the inhibition expected from such a water concentration (see Fig. 2), the autocatalytic acceleration seems to partly compensate for the negative effect of water and thus also play a major role in a CO₂/H₂ atmosphere. Hence, the net rate of the reaction is determined by the balance between acceleration from the autocatalytic pathway and inhibition

from produced water, which will depend on the reaction conditions such as the composition of the syngas.

We show here for the first time that methanol formation over the industrially applied Cu/ZnO/Al₂O₃ catalysts is dominated by an autocatalytic pathway that involves methanol. At high SV the formed methanol is almost exclusively from CO₂ with the industrial Cu/ZnO/Al₂O₃ catalyst^[9, 13, 14]. This is most likely also the case at lower SV, where the rate from a CO₂-containing gas (> 5 g_{MeOH}/g_{cat.}/h in Fig. S1c) is also far higher than in a CO/H₂ feed (0.4 g_{MeOH}/g_{cat.}/h at comparable conditions^[9]). The autocatalytic pathway at lower SV must therefore be expected to proceed from CO₂. At lower SV/higher conversion with greater water formation more methanol is formed by the CO→CO₂→CH₃OH sequence of R2 followed by R1, but the constancy in CO₂ concentration across the reactor (Fig. S2) suggests that R2 is fast, and consequently R1 is solely rate limiting in methanol synthesis. Adsorbed formate is present on the metal surface at methanol synthesis conditions^[14, 21, 22], which suggests that the autocatalytic pathway could involve CO₂-derived formate. Fig. 4a shows that CD₃OOCH was formed at low temperature, when Cu/ZnO/Al₂O₃ with pre-adsorbed HCOO (from exposure to HCOOH/N₂ at 303 K) was subjected to temperature programmed reaction (TPR) in a flow of CD₃OD in He. This illustrates that methyl formate can be formed from reaction between methanol and surface formate. A role of molecularly adsorbed formic acid cannot be fully excluded here, but previous IR studies^[23, 24] also demonstrate that the ester is easily formed by reaction of an alcohol with adsorbed formate at typical methanol synthesis temperatures. A probable pathway for the autocatalytic process is therefore via formation of the methyl formate ester from methanol and surface formate (R3) followed by hydrogenation of the ester (R4). However, methyl formate may also be decarbonylated to methanol and CO (R5)^[25].



Reaction R3 followed by reaction R4 results in a net gain of methanol, whereas the combination of R3 and R5 yields no net gain. Effective autocatalysis via methyl formate therefore relies on the rates of R3 and R4 being faster than direct CO₂ hydrogenation and on a high selectivity to hydrogenation (R4) relative to decarbonylation (R5) in the conversion of methyl formate. Fig. 4b shows the results, when Cu/ZnO/Al₂O₃ pre-covered with surface formate (from HCOOH) was subjected to a TPR in a flow of either CH₃OH/He or H₂. Fig. 4b illustrates that the onset of methyl formate formation in a CH₃OH/He gas occurs at a lower temperature than methanol formation in H₂. Re-adsorption phenomena can delay the appearance of a product in a TPH, but the lower onset temperature does indicate that R3 is considerably faster than direct hydrogenation of HCOO, and there are good indications in the literature that this is also the case for both R4 and R5. Fakley and co-workers^[26] used the data from Monti et al.^[25] to calculate that R4 should be of ample rate on Cu to account for an acceleration of the methanol synthesis.

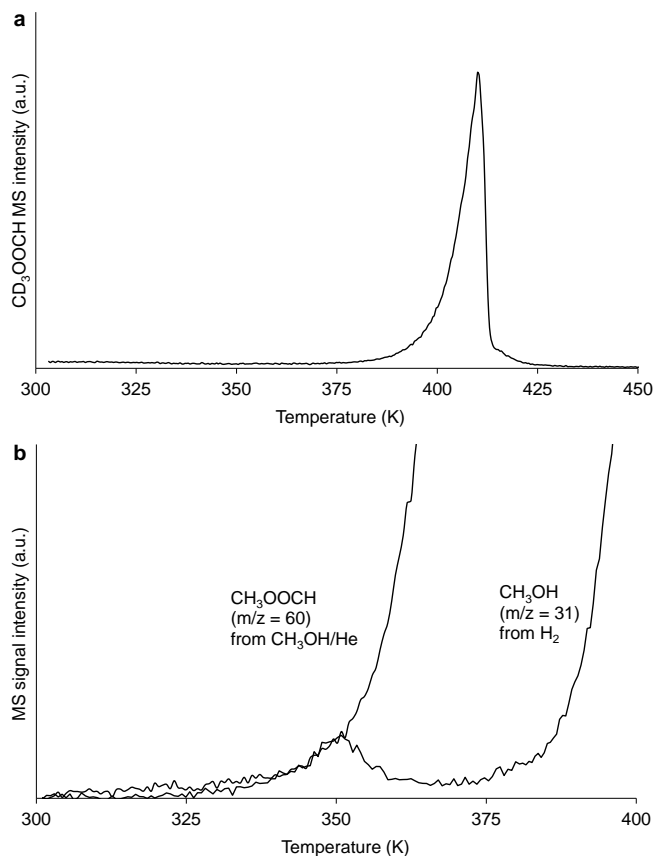


Fig. 4. (a) The formation of methyl formate (CD_3OOCH , $m/z = 63$) as a function of temperature during TPR when $HCOO$ -covered $Cu/ZnO/Al_2O_3$ was heated (1 K/min) at 1 atm in a 19 NmL/min flow of 4.1 mol% CD_3OD in He, 0.5 g cat. See Fig. S7 for details on peak shape. **(b)** Comparison of the onset of methyl formate formation during TPR in 5.5 mol% CH_3OH in He and the onset of methanol formation during TPR in 100% H_2 when formate covered $Cu/ZnO/Al_2O_3$ was subjected to TPR at 1 atm. Ramp: 1 K/min, Flow: 40 NmL/min, 0.5 g cat.

Santiago et al.^[27] co-fed methyl formate with the synthesis gas, and their results showed that methyl formate was rapidly converted over $Cu/ZnO/(Al_2O_3)$ and Cu/Al_2O_3 catalysts at 473 K and 65 bar. We infer from their data that the additional production of methanol due to methyl formate co-feeding was almost twice as high for $Cu/ZnO/Al_2O_3$ compared to Cu/Al_2O_3 , which suggests a preference for R4 on $Cu/ZnO/Al_2O_3$ and a preference for R5 on Cu/Al_2O_3 . A preference for R5 on Cu/Al_2O_3 is further supported by the results of Lam et al.^[23], who observed decarbonylation of methyl formate over Cu/Al_2O_3 and found that R5 is catalysed by the Al_2O_3 support. By contrast, Cu/ZnO -systems^[28] and Cu/SiO_2 -systems^[25] preserve a high selectivity to R4 versus R5 also at high temperatures, possibly because these supports are less likely to catalyse R5. A pathway via methyl formate would thus explain the observed support dependence in Fig. 1: i.e. a net acceleration with increasing conversion for the $Cu/ZnO/(Al_2O_3)$ and Cu/SiO_2 systems, where R4 dominates, whereas R5 dominates for Cu/Al_2O_3 and interrupts the autocatalytic pathway. As previously discussed, the net rate is governed by the competition between the autocatalytic acceleration and the water inhibition. Consequently, the conversion independent TOF of Cu/Al_2O_3 in Fig. 1 does not rule out that the autocatalytic pathway proceeds to some extent for Cu/Al_2O_3

and partly compensates for inhibiting effects of water, but the efficacy of the autocatalytic pathway is clearly lower for Cu/Al₂O₃ than for the Cu/ZnO(/Al₂O₃) and Cu/SiO₂ systems.

A consequence of the support dependence in the autocatalytic pathway is that conclusions regarding the difference in TOF between Cu/ZnO(/Al₂O₃) and Cu/Al₂O₃ are highly dependent on the conditions. Fig. 1 shows that the ratio between their TOF-values increases from a factor of three at differential conditions to more than an order of magnitude at higher conversion. Such variations illustrate the complexity that can emerge in catalytic reactions due to the existence of multiple, parallel reaction pathways with varying dependence on conditions and catalyst composition. This new and more complex picture of the reaction routes over Cu based methanol synthesis catalysts can possibly help to reconcile some apparent disparities between previous conclusions in the literature. Such complexity arising from the existence of multiple reaction pathways should be a general consideration for catalytic processes, since methanol synthesis may not be the only reaction, where multiple, parallel pathways coexist.

Conclusion

The discovery of a previously unknown autocatalytic mechanism dominating methanol synthesis at commercial reaction conditions with the industrial catalyst satisfactorily explains the so far unexplained observations^[6, 7] of increasing methanol synthesis rates with increasing conversion. This novel understanding represents a paradigm shift in the mechanistic interpretation of methanol synthesis and shows that important new discoveries can be made even for well-studied and widely applied catalyst systems. Finally, this breakthrough paves the way for further understanding, improvements and process optimization of industrial methanol synthesis.

Acknowledgements

This work was supported by a research grant (9455) from VILLUM FONDEN. We thank Saint Gobain for providing the SiO₂ support.

References

- [1] J. Sehested, *J. Catal.* **2019**, *371*, 368-375.
- [2] T. Fujitani, M. Saito, Y. Kanai, T. Kakumoto, T. Watanabe, J. Nakamura, T. Uchijima, *Catal. Lett.* **1994**, *25*, 271-276.
- [3] M. Saito, K. Murata, *Catal. Survey Asia* **2004**, *8*, 285-294.
- [4] R. Burch, S. E. Golunski, M. S. Spencer, *J. Chem. Soc. Faraday Trans.* **1990**, *86*, 2683-2691.
- [5] I. Nakamura, T. Fujitani, T. Uchijima, J. Nakamura, *J. Vac. Sci. Technol. A* **1996**, *14*, 1464-1468.
- [6] J. S. Lee, S. H. Han, H. G. Kim, K. H. Lee, Y. G. Kim, *Korean J. Chem. Eng.* **2000**, *17*, 332-336.
- [7] M. Sahibzada, I. S. Metcalfe, D. Chadwick, *J. Catal.* **1998**, *174*, 111-118.
- [8] O. Cherifi, S. Monteverdi, M. M. Bettahar, M. Forissier, V. Perrichon, *Bull. Soc. Chim. Fr.* **1985**, 405-409.
- [9] N. D. Nielsen, J. Thrane, A. D. Jensen, J. M. Christensen, *Catal. Lett.* **2020**, *150*, 1427-1433.
- [10] Y. Yang, C. A. Mims, D. H. Mei, C. H. F. Peden, C. T. Campbell, *J. Catal.* **2013**, *298*, 10-17.
- [11] R. Chatterjee, S. Kuld, R. van den Berg, A. Chen, W. Shen, J. M. Christensen, A. D. Jensen, J. Sehested, *Top. Catal.* **2019**, *62*, 649-659.
- [12] G. H. Graaf, J. G. M. Winkelman, *Ind. Eng. Chem. Res.* **2016**, *55*, 5854-5864.

- [13] G. C. Chinchén, P. J. Denny, D. G. Parker, M. S. Spencer, D. A. Whan, *Appl. Catal.* **1987**, *30*, 333-338.
- [14] N. D. Nielsen, A. D. Jensen, J. M. Christensen, *Catal. Lett.* in press, DOI: <https://doi.org/10.1007/s10562-020-03162-7>.
- [15] W.-H. Cheng, H. H. Kung (Eds.), *Methanol production and use*, CRC Press **1994**.
- [16] J. Słoczyński, R. Grabowski, J. Janas, J. Skrzypek, *Chem. Eng. Sci.* **1991**, *46*, 2599-2610.
- [17] A. Tarasov, F. Seitz, R. Schlögl, E. Frei, *ACS Catal.* **2019**, *9*, 5537-5544.
- [18] L. Fan, Y. Sakaiya, K. Fujimoto, *Appl. Catal. A* **1999**, *180*, L11-L13.
- [19] N. Tsubaki, M. Ito, K. Fujimoto, *J. Catal.* **2001**, *197*, 224-227.
- [20] P. Reubroycharoen, T. Yamagami, T. Vitidsant, Y. Yoneyama, M. Ito, N. Tsubaki, *Energy Fuels* **2003**, *17*, 817-821.
- [21] S. Lin, A. Oldfield, D. Klenerman, *Surf. Sci.* **2000**, *464*, 1-7.
- [22] F. Le Peltier, P. Chaumette, J. Saussey, M. M. Bettahar, J. C. Lavalley, *J. Mol. Catal. A* **1998**, *132*, 91-100.
- [23] E. Lam, J. J. Corral-Perez, K. Larmier, G. Noh, P. Wolf, A. Comas-Vives, A. Urakawa, C. Coperet, *Angew. Chem. Int. Ed.* **2019**, *58*, 13989-13996.
- [24] R. Yang, Y. Zhang, N. Tsubaki, *Catal. Commun.* **2007**, *8*, 1829-1833.
- [25] D. M. Monti, M. S. Wainwright, D. L. Trimm, N. W. Cant, *Ind. Eng. Chem. Prod. Des. Dev.* **1985**, *24*, 397-401.
- [26] M. E. Fakley, J. R. Jennings, M. S. Spencer, *J. Catal.* **1989**, *118*, 483-486.
- [27] M. Santiago, K. Barbera, C. Ferreira, D. Curulla-Ferré, P. Kolb, J. Pérez-Ramírez, *Catal. Commun.* **2012**, *21*, 63-67.
- [28] G. Braca, A. M. R. Galletti, N. J. Laniyonu, G. Sbrana, E. Micheli, M. Di Girolamo, M. Marchionna, *Ind. Eng. Chem. Res.* **1995**, *34*, 2358-2363.