



Correlating Surface Strain with Activity in Commercial Platinum Catalysts

Kelly, Daniel J.; Brandes, Benedikt A.; Liu, Pei; Hansen, Thomas W.

Published in:
Microscopy and Microanalysis

Link to article, DOI:
[10.1017/S1431927622009928](https://doi.org/10.1017/S1431927622009928)

Publication date:
2022

Document Version
Peer reviewed version

[Link back to DTU Orbit](#)

Citation (APA):
Kelly, D. J., Brandes, B. A., Liu, P., & Hansen, T. W. (2022). Correlating Surface Strain with Activity in Commercial Platinum Catalysts. *Microscopy and Microanalysis*, 28(S1), 2610-2611.
<https://doi.org/10.1017/S1431927622009928>

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Correlating Surface Strain with Activity in Commercial Platinum Catalysts

Daniel J. Kelly^{1*}, Benedikt A. Brandes², Pei Liu¹ and Thomas W. Hansen¹

¹ DTU Nanolab, Technical University of Denmark, Kgs. Lyngby 2800, Denmark

² DTU Energy, Technical University of Denmark, Kgs. Lyngby 2800, Denmark

* Corresponding author: dankel@dtu.dk

The introduction of another species, usually a transition metal or lanthanide, into platinum to form a bimetallic particle of composition causes expansion or contraction of Pt-Pt bond distances, altering the chemisorption energy of the nanoparticle and thus its performance of as a catalyst. Based on this principle, alloyed platinum nanoparticles are employed as highly efficient electrocatalysts for the oxygen reduction reaction that underpins the operation of hydrogen fuel cells [1]. The catalytic activity of such particles is highly dependent on their composition and structure, with the relationship between performance and activity across alloys of different elements typically presented as a volcano plot. Typically the strain is measured non-locally, for example using X-ray diffraction (XRD) to measure the average Pt-Pt over thousands of individual particles. However the small size of particles (1 – 2 nm) and non-uniformity of true commercial catalyst distribution means the XRD-measured strain may not be precise enough to establish a solid structure-performance dependence.

In this work we use high resolution scanning transmission electron microscopy (STEM) to gain new insight into the localization of strain in a range of commercial platinum alloyed nanoparticles Pt₃M/C (where M = Co, Fe, Ni, Cr, Cu, Sn). The nanoparticles ranged between 0.5 – 5 nm in radius and are dispersed on a carbon black support (fig 1A). A probe-corrected STEM (sub-Ångstrom resolution) in angular annular dark field (HAADF) mode enables visualization of the atomic columns of each nanoparticle, with no apparent variation in contrast between columns confirming the presence of a solid solution (fig. 1B). To ensure that the pristine nanoparticles are representative of the working catalysts, imaging of acid-treated and post-cycling particles was performed, revealing minimal structural and compositional change.

To investigate possible localized strain that may be beyond the sensitivity of XRD, we use perform strain mapping on high resolution STEM micrographs. This was achieved through a set of preprocessing steps (stack alignment, Wiener filter and Fourier filtering), followed by identification of atomic column positions using atomap [2] and subsequent measurement of the nearest neighbor columns for each position (fig 1C). In order to establish a metric for the proximity of a specific atomic column to the surface of the nanoparticle (in the x-y plane), we label each column with a layer index (fig 1D). Comparing these metrics across approximately 10-20 particles of each of the six alloys, in addition to the pure Pt/C nanoparticle, reveals a small positive strain at the surface of the nanoparticles that rapidly drops off with increasing layer depth. The relation is shown for a representative Pt₃Co/C nanoparticle in fig. 2A.

Using this distribution, the volcano plot for these specific Pt₃M/C alloys can be refined by establishing a layer depth threshold. Considering all atomic columns, the alloys are well-aligned with XRD data (both experimental and literature), where the polycrystalline Pt activity is excluded from even the most general trends. However considering only atomic columns from the outermost layers, to which oxygen is chemisorbed during reduction, a qualitatively better fit is obtained with the theoretical values predicted

in literature, as well as the experiment polycrystalline value (fig. 2B).

We expect that this methodology, where the relative position of atoms within a nanostructure can be indexed and correlated with physical or chemical measurements, will be useful for future studies concerning surface kinetics and may serve as an auxiliary technique to the typical bulk analysis of nanostructures.

References:

[1] J. Greeley et al., *Nature Chem* **1** (2009), p. 552–556. <https://doi.org/10.1038/nchem.367>

[2] M. Nord et al. *Advanced structural and chemical imaging* **3**, 9 (2017), p. 1-12.

<https://doi.org/10.1186/s40679-017-0042-5>

[3] M. Escudero-Escribano et al. *Science* **352**, 6281 (2016), p. 73-76.

<https://doi.org/10.1126/science.aad8892>

[4] The authors acknowledge funding from the Danish National Research Foundation Center of Excellence for Nanostructured Graphene (DNRF103)

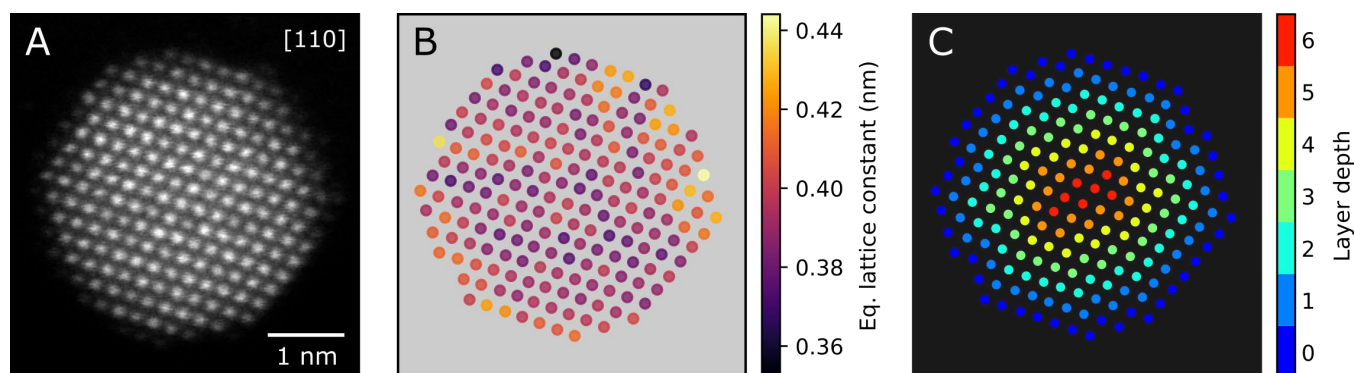


Figure 1. Strain mapping and layer labelling for a representative $\text{Pt}_3\text{Co}/\text{C}$ nanoparticle. A) Experimental HAADF-STEM micrograph, B) map of equivalent lattice constant computed from Pt-Pt distances, C) layer depth labels

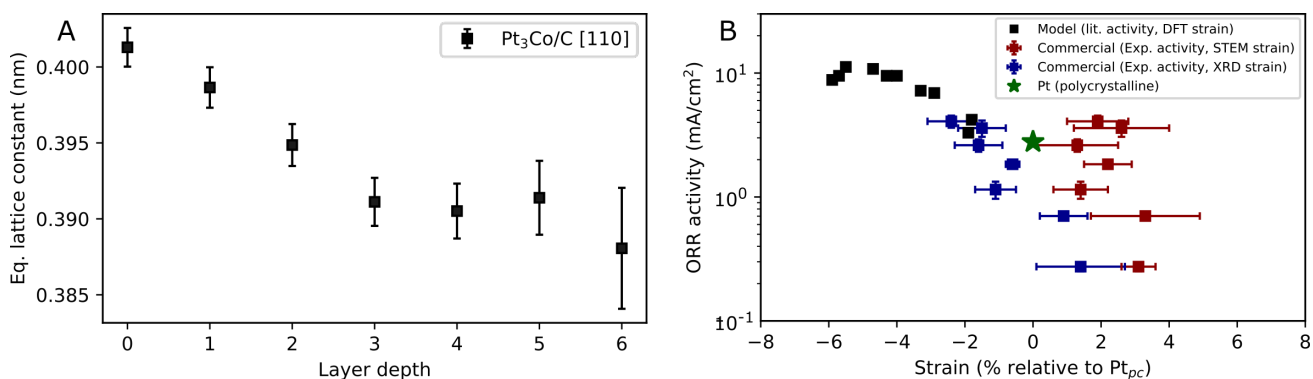


Figure 2. Correlation of strain and position relative to the nanoparticle surface. A) Equivalent lattice constant vs. layer depth for the nanoparticle in figure 1. B) Refined volcano plot incorporating data from model catalysts in literature (strain computed via DFT) [3] and commercial catalysts (strain measured by XRD and STEM). Only atomic columns at the surface (layer depth ≤ 1) are considered for the STEM data.