



Chemical preparation and spectroscopic characterization of plasmonic silver nanoparticles using fruits as reducing agent.

Hyllested, J.Æ.; Espina Palanco, Marta; Hagen, N.; Mogensen, Klaus Bo; Kneipp, Katrin

Published in:

Proceedings of the 24th International Conference on Raman Spectroscopy

Publication date:

2014

[Link back to DTU Orbit](#)

Citation (APA):

Hyllested, J. Æ., Espina Palanco, M., Hagen, N., Mogensen, K. B., & Kneipp, K. (2014). Chemical preparation and spectroscopic characterization of plasmonic silver nanoparticles using fruits as reducing agent. In *Proceedings of the 24th International Conference on Raman Spectroscopy*

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Chemical preparation and spectroscopic characterization of plasmonic silver nanoparticles using fruits as reducing agent.

J. Æ. Hyllested^a, M. E. Palanco^a, N. Hagen^a, K. B. Mogensen^b,
K. Kneipp^a.

^a Technical University of Denmark, Department of Physics. 2800 Kgs. Lyngby, Denmark.

^b Technical University of Denmark, Department of Micro- and Nanotechnology. 2800 Kgs. Lyngby, Denmark.

Silver and gold nanoparticles (NPs) have gained a lot of interest in recent years due to a wide range of applications. As a very important property, these metal NPs exhibit strong surface plasmon resonances in the optical range. Coupling between surface plasmons and light results in high local fields in the vicinity of the NPs. These enhanced local fields open up exciting capabilities for probing and sensing, in particular also in fields such as medicine and biology. Therefore, NPs should be free of toxic chemicals, which are often used in conventional chemical preparation methods [1]. There are several approaches during the recent years which have shown that plant extracts can act as reducing and capping agents for the synthesis of metal NPs. Green synthesis does not require any toxic chemicals in the synthesis of the NPs, which makes it eco-friendly and very attractive [2, 3]. The use of biological entities for generation of NPs can be a rapid, sensitive and selective method [4].

Here we report the synthesis of silver NPs from silver nitrate. Pineapples and oranges deliver the reducing agents (figure 1).

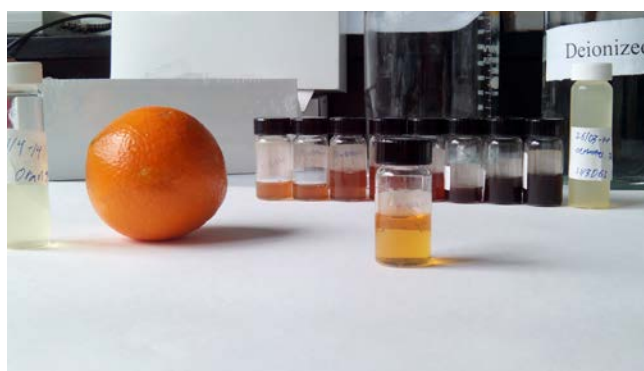


Figure 1 Silver nanoparticles made from orange and pineapple extracts.

Fruit extracts were collected directly from the pineapple or had been extracted from orange peels in a boiling process [5].

The formation of silver nanoparticles starts after 1mM AgNO₃ was added to the fruit extract in volume ratios of approximately 10:1.

Size and shape of the particles are characterized by electron microscopy. The reduction process and the formation of nanoparticles can be monitored by UV–visible spectroscopy using the increase of the surface plasmon absorption band.

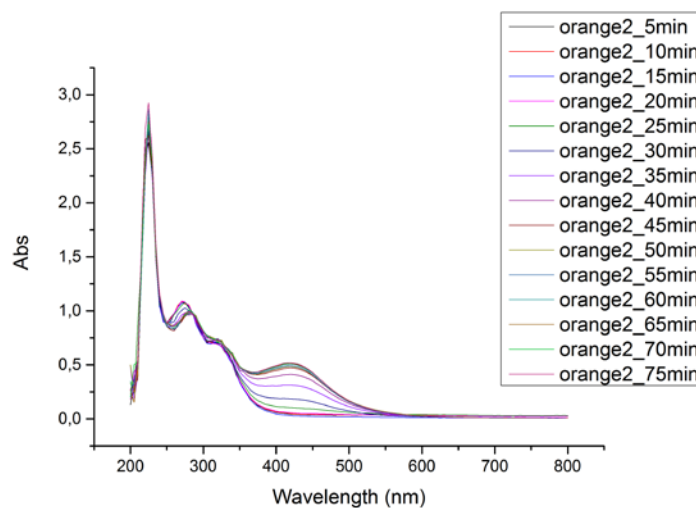


Figure 2 Time development of the surface plasmon band around 420 nm during the reduction process.

Figure 2 shows the characteristic band growing over 75 minutes. In addition, over time, we observed a small red shift of the surface plasmon resonance which indicates the formation of slightly bigger NPs.

In our experiments, pineapples and oranges result in differently shaped silver NPs. By changing the concentration of the extracts, the reduction time, size and morphology of the NPs can be altered.

REFERENCES

1. P.P.N. Vijay Kumara, S.V.N. Pammib, P. Kolluc, K.V.V. Satyanarayanad and U. Shameema, *Industrial Crops and Products*, 2014, **52**, 562-566.
2. V. K. Vidhu and D. Philip, *Spectrochim Acta A Mol Biomol Spectrosc*, 2014, **117**, 102-108.
3. K. D. Arunachalam and S. K. Annamalai, *Int. J. Nanomedicine*, 2013, **8**, 2375-2384.
4. M.R. Bindhu and M. Umadevi, *Spectrochim Acta A Mol Biomol Spectrosc*, 2014, **121**, 596-604.
5. S. Kaviya, J. Santhanalakshmi, B. Viswanathan, J. Muthumary, and K. Srinivasan. *Spectrochimica Acta Part A*, 2011, **79**, 594-598.